



A novel multinuclear solid state NMR approach for the characterization of kidney stones

César Leroy^{1,4}, Laure Bonhomme-Coury¹, Christel Gervais¹, Frederik Tielens^{1,7}, Florence Babonneau¹,
Michel Daudon², Dominique Bazin³, Emmanuel Letavernier², Danielle Laurencin⁴, Dinu Iuga⁵,
5 John V. Hanna⁵, Mark E. Smith⁶, Christian Bonhomme¹

¹Sorbonne Université, CNRS, Laboratoire Chimie de la Matière Condensée de Paris, LCMCP, F-75005 Paris, France.

²AP-HP, Hôpital Tenon, Explorations Fonctionnelles Multidisciplinaires et INSERM UMRS 1155, Sorbonne Université, Hôpital Tenon, Paris, France.

10 ³Institut de Chimie Physique, UMR CNRS 8000, Bâtiment 350, Université Paris Saclay, 91405 Orsay cedex, France & Laboratoire de Physique des Solides, UMR CNRS 8502, Bâtiment 510, Université Paris-Sud, 91405 Orsay cedex, France

⁴ICGM, Univ Montpellier, CNRS, ENSCM, Montpellier, France.

⁵Department of Physics, University of Warwick, Gibbet Hill Road, Coventry CV4 7AL, United Kingdom.

⁶Department of Chemistry, University of Southampton, Southampton SO17 1BJ, United Kingdom.

15 ⁷General Chemistry (ALGC) – Materials Modelling Group, Vrije Universiteit Brussel (Free University Brussels – VUB), Pleinlaan 2, 1050 Brussel, Belgium.

Correspondence to: Christian Bonhomme (christian.bonhomme@upmc.fr)

This article is dedicated to Geoffrey Bodenhausen on the occasion of his 70th Birthday.

Abstract. The spectroscopic study of pathological calcifications (including kidney stones) is extremely rich and helps to
20 improve the understanding of the physical and chemical processes associated with their formation. While FTIR imaging and optical/electron microscopies are routine techniques in hospitals, there has been a dearth of solid state NMR studies introduced into this area of medical research, probably due to the scarcity of this analytical technique in hospital facilities. This work introduces effective multinuclear and multi-dimensional solid state NMR methodologies to study the complex chemical and structural properties characterising kidney stone composition. As a basis for comparison three hydrates ($n = 1, 2$ and 3) of
25 calcium oxalate are examined along with nine representative kidney stones. The multinuclear MAS NMR approach adopted investigates the ^1H , ^{13}C , ^{31}P and ^{43}Ca nuclei, with the ^1H and ^{13}C MAS NMR data able to be readily deconvoluted into the constituent elements associated with the different oxalates and organics present. For the first time, the full interpretation of highly resolved ^1H NMR spectra is presented for the three hydrates, based on structure and local dynamics. The corresponding ^{31}P MAS NMR data indicates the presence of low-level inorganic phosphate species, however the complexity of these data
30 make the precise identification of the phases difficult to assign. This work provides physicians, urologists and nephrologists with additional avenues of spectroscopic investigation to interrogate this complex medical dilemma that requires real multi-technique approaches to generate effective outcomes.



1 Introduction

35 Kidney stones (KS) are a major health problem in industrialized countries. For example, the medical costs associated with the treatment of nephrolithiasis in France exceeds 800 million € annually. The study of KS is presently at the heart of a concerted multi-disciplinary axis of research involving physicians, physical chemists and spectroscopists (Bazin et al., 2016). Nevertheless, the nucleation and growth of KS remains largely unknown and the associated mechanism is based mainly on assumption and incomplete evidence; hence, more thorough and wide-ranging structural investigations are still required
40 (Sherer et al., 2018; Bazin et al., 2020). The growth of KS is clearly a multi-factorial problem, with their chemical composition and morphology presenting considerable variability due to the extreme complexity of the *in vivo* reaction media in which they are formed. The resultant biological materials exhibit very different characteristics as they can emanate from wide-ranging pathological scenarios including bacterial infection, genetic predispositions, mellitus diabetes and bowel diseases (Bazin et al., 2012). Hence, KS can be considered as real examples of hybrid organic-inorganic nanocomposite materials.

45 The main mineral components comprising hydrated calcium oxalates are the monohydrate $\text{CaC}_2\text{O}_4\cdot\text{H}_2\text{O}$ (whewellite, COM) and dihydrate $\text{CaC}_2\text{O}_4\cdot 2\text{H}_2\text{O}$ (weddellite, COD) species, although amorphous calcium oxalate can also be observed (Gehl et al., 2015; Ruiz-Agudo et al., 2017). The trihydrate form, $\text{CaC}_2\text{O}_4\cdot 3\text{H}_2\text{O}$ (caoxite, COT) is almost never observed *in vivo* but can be synthesized in aqueous solution. COD is characterized by a zeolitic structure exhibiting a true structural challenge. It is
50 considered as one of the very few *natural* MOFs (Metal Organic Frameworks) (Huskic, 2016; Dazem et al., 2019) and its chemical formula is better represented by $\text{CaC}_2\text{O}_4\cdot(2+x)\text{H}_2\text{O}$ ($x \leq 0.5$) (Petit et al., 2018). "Structural" and "zeolitic" water molecules are therefore distinguished. Calcium phosphates and other mineral phases can be detected as well in KS: hydroxyapatite ($\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$) which may be partially carbonated, brushite ($\text{CaHPO}_4\cdot 2\text{H}_2\text{O}$) or struvite ($\text{NH}_4\text{MgPO}_4\cdot 6\text{H}_2\text{O}$) (Gardner et al., 2021). The organic components (from few % to a major fraction) include e.g.: proteins
55 (collagen among them), uric acid, lipids, triglycerides, etc. The nature of the organic-inorganic interfaces remain largely unknown to date. This chemical and structural complexity at several scales requires the use of a wide variety of characterization methods. Recently, elaborate experiments took advantage of the last development in TEM (Transmission Electron Microscopy) (Gay et al., 2020) and of synchrotron radiation (Bazin et al., 2012). In hospitals, optical microscopy, FTIR, FTIR microscopy, SEM (Scanning Electron Microscopy) and X-ray diffraction are used in routine mode. Curiously, solid state NMR has been
60 used very rarely in the context of KS (and other pathological calcifications) apart from sparse ^{13}C and ^{31}P studies (Bak et al., 2000; Jayalakshmi et al., 2009; Reid et al., 2011; Reid et al., 2013; Li et al., 2016; Dessombz et al., 2016), unlike other human hard tissues such as bones and teeth. This is probably due to the fact that solid state NMR instruments are not widely available in hospital settings. It is also stressed that some KS are small so that the intrinsic lack of sensitivity associated to NMR may be a drawback. Other nuclei such as ^1H and ^{43}Ca can act as potential NMR targets. However, ^1H solid state NMR remains a
65 rather specialized technique because of the relative inefficiency of Magic Angle Spinning (MAS) in producing really high



resolution data from most systems. ^{43}Ca ($I = 7/2$) is particularly insensitive (as a result of its extremely low natural abundance, $\sim 0.14\%$, and low γ , $-1.8028 \cdot 10^7 \text{ rad}\cdot\text{s}^{-1}\cdot\text{T}^{-1}$, 57.2 MHz at 20 T).

In this work, a comprehensive multinuclear solid state NMR approach is presented facilitating the detailed structural analysis of KS and the related synthetic hydrated calcium oxalate phases (COM, COD, COT) associated with their composition. The synthetic phases were obtained by carefully controlling the precipitation of calcium salts in aqueous solutions as described below in section 7 (Leroy, 2016). Nine KS were studied systematically, some of them exhibiting similar NMR fingerprints. The spectra of five of them (KS1 \rightarrow KS5) are presented here. They come from the KS collection of Tenon hospital (Paris, France), led by Dr M. Daudon (the collection counts tens of thousands of samples from all origins exhibiting the largest variety of size, chemical composition and morphology worldwide). Our main goal here is to reach out to the physician's community and more specifically nephrologists, urologists and biologists. NMR methods are presented at moderate to high magnetic field (*i.e.* 7.0 to 16.4 T MHz) in order to make them much more widely accessible. Occasionally, further developments at ultra-high magnetic field (up to 35.2 T) are proposed to the user. Particular emphasis is placed on high-resolution ^1H MAS NMR with homonuclear decoupling and the complete interpretation of spectra based on structural data, and ^{43}Ca MAS NMR. To the best of our knowledge, these nuclei have never been used as spectroscopic probes for KS studies (apart for a unique ^{43}Ca MAS NMR study by Bowers and Kirkpatrick, 2011). A complete experimental protocol is then presented for the reconstruction of ^{13}C NMR spectra including organic/inorganic and/or rigid/mobile components. Finally, the intriguing role of phosphates in KS is partially deciphered by 2D ^1H - ^{31}P HETCOR MAS NMR experiments despite the low phosphate content in KS.


2 Quick and reliable assignment of hydrated calcium oxalate and organic phases by ^1H high resolution solid state NMR experiments

2.1 CRAMPS (Combined Rotation And Multiple Pulses Spectroscopy) approach

In terms of NMR sensitivity, ^1H greatly exceeds that of ^{13}C and ^{43}Ca . Moreover, it is an $I = 1/2$ nucleus, leading much more rapidly to quantitative data if relaxation delays are carefully set. It follows that ^1H is a target nucleus in the study of crystalline hydrated calcium oxalate phases and KS. Moreover, as KS are bio-nanocomposites, ^1H can be considered as a spectroscopic spy present both in the organic and inorganic components making the study of the interfaces eventually possible. In the absence of local dynamics, the strong ^1H - ^1H dipolar interaction is a major issue in ^1H solid state NMR leading to considerable broadening of the resonances. Current trends to reach the highest ^1H NMR resolution combine ultra-fast MAS, up to 111 kHz or above (Samoson, 2019) with ultra-high magnetic field, up to 35.2 T, (Gan et al., 2017) in order to average the strong dipolar couplings. Indeed, the homogeneous character of the homonuclear dipolar interaction implies poor MAS efficiency at low to moderate spinning frequencies (Schmidt-Rohr and Spiess, 1994) (note that the temperature increase, inside a 0.7 mm diameter rotor, is estimated to roughly 20 °C in the fast/ultra-fast regime, *i.e.* $\nu_{\text{rot}} > 30 \text{ kHz}$). This point is of prime importance as calcium oxalate structures may undergo subtle structural modifications upon heating (Deganello, 1981; Shepelenko, 2019) - see also



section 7). However, such leading-edge equipment is not widely available. An alternative is to use the CRAMPS sequence at moderate spinning frequency ($\nu_{\text{rot}} < 12$ kHz) (Paruzzo and Emsley, 2019). The DUMBO sequence (Decoupling Using Mind-
100 Boggling Optimization) belongs to the CRAMPS family (Lesage et al., 2003). Using this approach, the internal temperature increase remains moderate for all rotor diameters. Moreover, this methodology can be successfully implemented on almost all magnets. Moreover, larger rotor diameters may be used which can be interesting in terms of sensitivity. To the best of our knowledge, synthetic COM, COD and COT samples were never investigated by ^1H high resolution solid state NMR. The corresponding spectra are presented in Figure 1. At $\nu_{\text{rot}} = 12$ kHz, standard ^1H MAS NMR spectra (Figure 1a) are all
105 characterized by very broad and almost featureless lineshapes. Such spectral fingerprints are not useful for analytical purposes due to strong overlap of the resonances. DUMBO decoupling leads to a drastic increase in resolution and to very characteristic features for each synthetic hydrate.

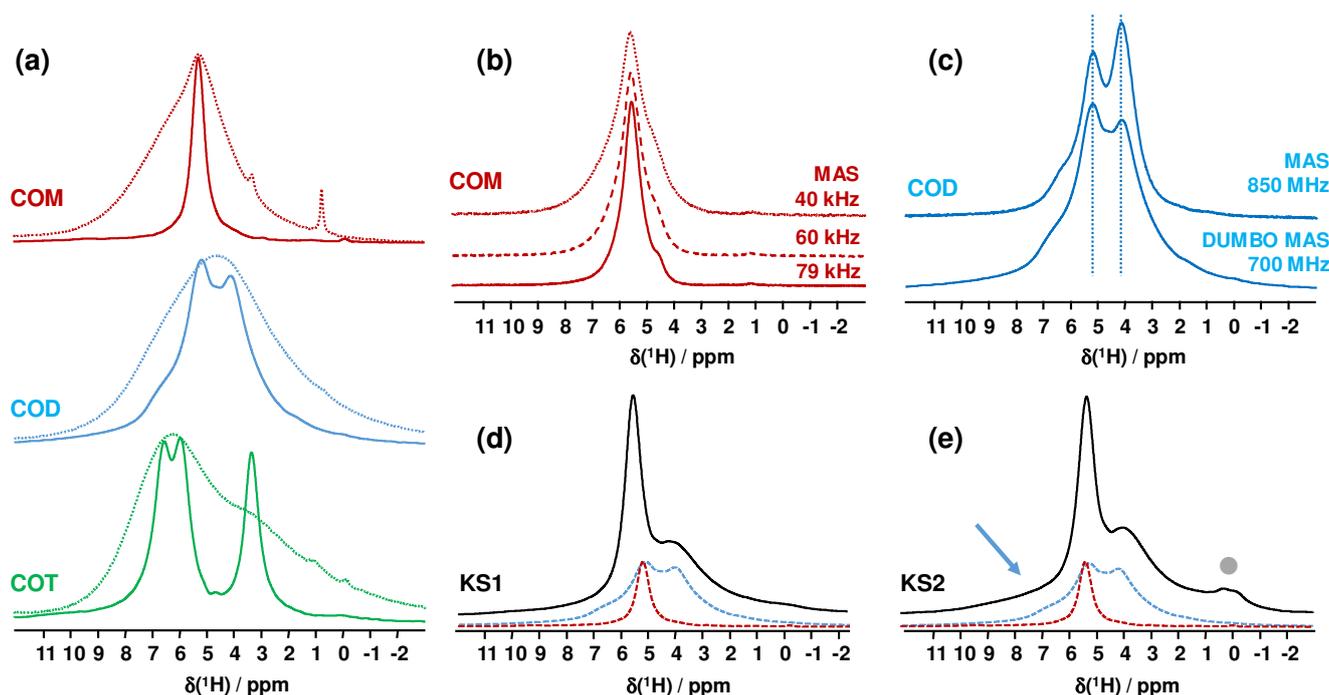


110 **Figure 1.** (a) ^1H MAS (dashed lines) and ^1H DUMBO MAS (solid lines) NMR spectra of COM (in red), COD (in blue), COT
(in green) ($\nu_{\text{rot}} = 12$ kHz, 700 MHz, 16.4 T). Only the isotropic resonances are represented. (b) ^1H very-fast MAS (40, 60 and
79 kHz) NMR spectra of COM at very high magnetic field (850 MHz). (c) Comparison of the ^1H NMR spectra of COD
obtained under DUMBO MAS ($\nu_{\text{rot}} = 12$ kHz, 700 MHz) and very-fast MAS ($\nu_{\text{rot}} = 79$ kHz, 850 MHz) conditions. Vertical
dashed lines are guidelines for the eyes. (d) ^1H DUMBO MAS NMR spectrum of KS1 ($\nu_{\text{rot}} = 12$ kHz, 700 MHz). The red and
blue dashed lines correspond to experimental ^1H DUMBO MAS NMR spectra of COM and COD, respectively. (e) ^1H DUMBO
115 MAS NMR spectrum of KS2 ($\nu_{\text{rot}} = 12$ kHz, 700 MHz). The plain light grey circle indicates the presence of organic



components in KS2. The blue arrow indicates the superposition of organic components (aromatic region) and the deshielded shoulder of COD.

120 The COT crystallographic structure exhibits six inequivalent sites for protons (Heijnen, 1985) whereas only three resonances are clearly observed at $\delta_{\text{iso}}(^1\text{H}) = 3.36, 5.95$ and 6.53 ppm (Figure 1a). A realistic assumption is that some resonances are so close that they cannot be distinguished even under DUMBO decoupling. It has been previously shown (Eckert et al., 1988; Pourpoint et al., 2007) that $\delta_{\text{iso}}(^1\text{H})$ can be related to the *shortest* $\text{O}-\underline{\text{H}}\cdots\underline{\text{O}}$ bond length in hydrogen bond networks. The general trend is that $\delta_{\text{iso}}(^1\text{H})$ strongly increases with the shortening of $\text{O}-\underline{\text{H}}\cdots\underline{\text{O}}$. Interestingly, the six non equivalent hydrogens can be
125 distinguished based on $\text{O}-\underline{\text{H}}\cdots\underline{\text{O}}$ distances, leading to three distinct groups (Figure 2 and Table S1): $1.668\text{-}1.679 \text{ \AA} / 1.809\text{-}1.837 \text{ \AA} / 1.957\text{-}1.978 \text{ \AA}$. It is stressed here that the distances were obtained after extensive optimization of the geometry of the COT structure at DFT level (the same comment holds for COM and COD structures, see section 7). According to the literature (Pourpoint et al., 2007), a variation of $\text{O}-\underline{\text{H}}\cdots\underline{\text{O}}$ of $\sim 0.3 \text{ \AA}$ is related to a $\delta_{\text{iso}}(^1\text{H})$ variation of ~ 3.5 ppm, in rather good agreement with the results presented here (the shorter the distance, the higher the isotropic ^1H chemical shift). We mention
130 also (Table S1) that each proton of the structure is involved in a relatively high number of $\underline{\text{H}}\cdots\underline{\text{O}}$ contacts (from 3 to 4 with $\text{O}-\underline{\text{H}}\cdots\underline{\text{O}} \leq 3 \text{ \AA}$). The 3 \AA cut-off is realistic when considering "weak" H-bonds (Steiner, 2002). In other words, the shortest $\text{O}-\underline{\text{H}}\cdots\underline{\text{O}}$ distance dictates directly $\delta_{\text{iso}}(^1\text{H})$, whereas the number of $\underline{\text{H}}\cdots\underline{\text{O}}$ contacts is more representative of the electrostatic/dispersion contributions at a given H position (Steiner, 2002). As all protons of COT are characterized by a large number of $\underline{\text{H}}\cdots\underline{\text{O}}$ contacts, we assume a certain character of "rigidity" of the structure at room temperature and very limited
135 local dynamics (Figure 3c). Under this simple assumption, at most three resolved $\delta_{\text{iso}}(^1\text{H})$ are expected due to similarities in $\text{O}-\underline{\text{H}}\cdots\underline{\text{O}}$ distances (see above), in good agreement with the experimental data (Figure 1a). Therefore, the ^1H COT assignments are the following, using the numbering given in Table S1: H1/H6: 3.36 ppm, H3/H5: 5.95 ppm, H2/H4: 6.53 ppm. We note that partial deuteration could be of great help to increase further the resolution.

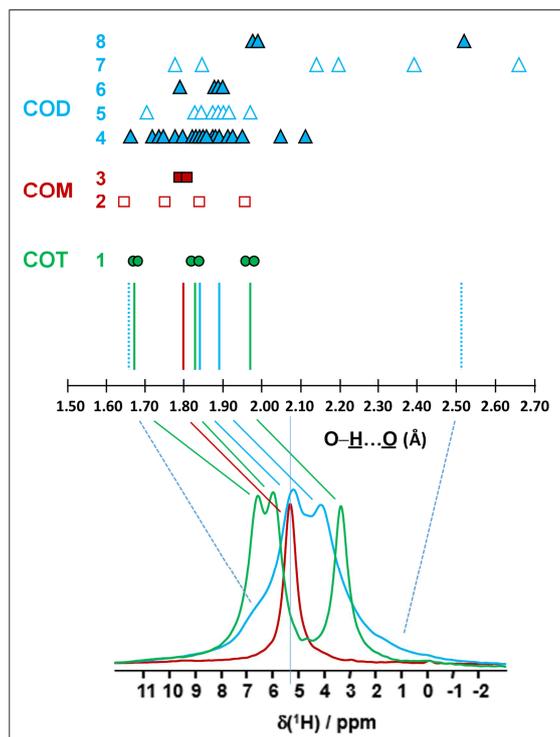

140

Figure 2. Prediction of the relative positions of $\delta_{\text{iso}}(^1\text{H})$ for COM (red), COD (blue) and COT (green) as function of the shortest O-H...Q distances (in Å). General rules: (i) for a given O-H...Q distance, a $\delta_{\text{iso}}(^1\text{H})$ is associated (vertical colored solid lines), (ii) if local dynamics are present, averaged O-H...Q distances are first calculated. All distances are derived from optimized geometries at the DFT level (Table S1 and section 7). The effect of eventual local dynamics in the case of "less rigid" structure is taken into account. **Line 1:** the structure of COT is considered as "rigid" (plain green circles). On the basis of the shortest O-H...Q distance, the six inequivalent protons can be associated in three groups. To each group, a single average $\delta_{\text{iso}}(^1\text{H})$ is assigned. A total of three lines for COT is predicted (represented by the three vertical green solid lines). **Line 2:** the structure of COM is considered as "less rigid" (open squares). **Line 3:** the corresponding averaged distances are represented by plain squares. A single average $\delta_{\text{iso}}(^1\text{H})$ is associated as the averaged distances are very close. A total of one line for COM is predicted. **Lines 4 to 8:** The COD case: COD exhibits both "rigid" (plain triangles, **Line 4**) and "less rigid" water molecules (open triangles, **Line 5** for the four structural water molecules and **Line 7** for the three zeolitic water molecules.). **Line 6:** the corresponding averaged distances for the structural water molecules are represented by plain triangles. **Line 8:** the corresponding averaged distances for the zeolitic water molecules are represented by plain triangles. A continuum of $\delta_{\text{iso}}(^1\text{H})$ is predicted for COM. The vertical blue dashed lines correspond to the expected limits of $\delta_{\text{iso}}(^1\text{H})$. The two vertical solid blue lines correspond to local maxima adding **Lines 4, 6** and **8**. Bottom: the superposition of the ^1H DUMBO MAS NMR spectra for COM (red), COD (blue) and COT (green) (Figure 1a). The solid and dashed lines connect the experimental data and the predicted $\delta_{\text{iso}}(^1\text{H})$.

155



Figure 3. Structural details of COM (a), COD (b) and COT (c). For each proton of the water molecules, the shortest O-H...O distance (in Å) is represented as well as the number of H...O contacts (cut-off: 3 Å). For COT, the number of H...O contacts is high (3 to 4): the COT structure is considered as "rigid". In the case of COD, the structural and *zeolitic* water molecules are represented in blue and green, respectively. A selection of "rigid" (H4) and "less rigid" (H33/H34) water molecules is presented. All distances and number of H...O contacts are summarized in Table S1. Color code: red: O, black: C, light pink: H.

The ^1H spectrum of COD (Figure 1a) is *a priori* complex as it corresponds to the superposition of structural and *zeolitic* water molecules (Tazzoli and Domeneghetti, 1980; Izatulina et al., 2014). It is much broader than the spectra corresponding to COM and COT. More specific features centred at $\delta_{\text{iso}}(^1\text{H}) = 4.11, 5.17$ and ~ 6.5 (shoulder) ppm are observed (Figure 1a). When compared to the COT spectrum, the spectral resolution decreases as expected from the partial disorder of the *zeolitic* water molecules. The detailed examination of selected O-H...O distances in detail (Table S1) allowed proposing a partial assignment of the resonances. For that purpose, a model (relaxed at the DFT level) which corresponds to $\text{CaC}_2\text{O}_4(2+0.375)\text{H}_2\text{O}$ was first calculated (or, $\text{Ca}_8\text{C}_{16}\text{O}_{32}(\text{H}_2\text{O})_{16}(\text{H}_2\text{O})_3$). The water molecules located in the channels of the *zeolitic* structure are represented in *italic*. Taking into account the number of H...O contacts (in full analogy with the approach described above for COM and COT), among the 19 water molecules, 7 molecules are considered as "less rigid" (or, potentially mobile) out of which 4 of them are structural and 3 are *zeolitic*. The remaining 12 water molecules are considered as "rigid". Typical example of "rigid" (H4) and "less rigid" (H33/H34) water molecules are presented in Figure 3b. From Figure 2, it is then possible to predict the expected ranges of $\delta_{\text{iso}}(^1\text{H})$ for COD. The rules applied are that "rigid" water molecules correspond to two distinct $\delta_{\text{iso}}(^1\text{H})$ (Line 4), whereas "less rigid" water molecules correspond to a single average $\delta_{\text{iso}}(^1\text{H})$ (averaging of Line 5 gives Line 6 and averaging of Line 7 gives Line 8). The sum of Lines 4, 6 and 8 (in blue) corresponds to the expected ^1H spectrum for COD. On this basis, it is expected: (i) that $\delta_{\text{iso}}(^1\text{H})$ is distributed over a much larger range when compared to COM and COT, (ii) that some maxima should be observed (at least two, corresponding to large number of overlapping triangles in Figure 2). Points (i) and (ii) are in very good agreement with experimental observations. All in all, the relative predicted positions for $\delta_{\text{iso}}(^1\text{H})$ resonances are in agreement with the experimental data for COM, COD and COT (bottom of Figure 2), validating the proposed assignments.

As a first conclusion of this section, ^1H DUMBO MAS NMR spectra for COM, COD and COT correspond to useful fingerprints for analytical purposes as they are clearly characteristic for each phase. Such fingerprints can be used for the analysis of ^1H NMR spectra of KS (see below). We emphasize that ^1H spectra with excellent signal-to-noise ratio were obtained within minutes. As $\delta_{\text{iso}}(^1\text{H})$ values are very sensitive to H-bond networks as well as to local motional averaging, studies performed on synthetic COM, COD and COT were necessary prior to the detailed analyses of KS. Nevertheless, some comments have to be made at this stage: (i) First, the ^1H DUMBO MAS methodology ($\nu_{\text{rot}} = 12$ kHz, 700 MHz) is comparable to the very-fast MAS/very-high magnetic field approach ($\nu_{\text{rot}} \sim 80$ kHz, 850 MHz) without any multiple pulses decoupling. In




205 Figure 1b, the ^1H MAS NMR spectra of COM are presented at various fast/very-fast rotation frequencies, from $\nu_{\text{rot}} = 40$ to
~ 80 kHz. As in the case of the DUMBO MAS approach, a single resonance (with a small shoulder) was observed, showing a
continuously decreasing linewidth with increasing the MAS frequency. The linewidth obtained at ~ 80 kHz is still broader
than the one observed under DUMBO MAS conditions. In Figure 1c, the two approaches are compared in the case of COD.
The resolution is slightly enhanced under very-fast MAS at 79 kHz but remains comparable to DUMBO conditions at 12 kHz.
210 More importantly, the relative intensities are not strictly preserved indicating that some distortions of the lineshapes may occur
under DUMBO conditions. It follows that only semi-quantitative data can be extracted at best in the case of complex mixtures
of hydrated calcium oxalate phases. Moreover, dynamics at room temperature may impact the efficiency of the DUMBO
decoupling.

215 Finally, two KS (KS1 and KS2) were studied by ^1H DUMBO MAS NMR (Figures 1d and 1e). In the case of KS1, a mixture
of COM and COD is immediately detected (in full agreement with FTIR and powder XRD, not shown here). As stated above,
a slight deviation of $\delta_{\text{iso}}(^1\text{H})$ for COM is observed. A semi-quantitative analysis of the COM/COD proportions is possible and
could be systematically compared to FITR analyses (as routinely obtained in hospitals). In addition to COM and COD
resonances, the ^1H DUMBO MAS NMR spectrum of KS2 exhibits small new contributions that can be attributed to organic
220 moieties (such as proteins). In this case, a semi-quantitative analysis of the KS appears more difficult to perform. Working at
much higher magnetic field, 35.2 T (Gan et al., 2017), and under ultra-fast MAS ($\gg 100$ kHz) should lead to increased
resolution and easier direct quantification of the spectra.

2.2 $T_2^*(^1\text{H})$ editing and ^1H - ^1H DQ experiments

225 Another KS sample, KS3, that was studied contained a large proportion of organic moieties (as shown by FTIR). Another
option to increase ^1H NMR resolution is to implement standard Hahn echoes with increasing delays, τ , (up to several ms) and
synchronization with the MAS frequency. The magnetization associated to protons characterized by short $T_2^*(^1\text{H})$ will dephase
very rapidly. ^1H MAS echoes ($\nu_{\text{rot}} = 30$ kHz) for KS3 are presented in Figure 4. From powder XRD data (not shown here)
confirmed by ^{13}C CP MAS NMR data (see section 4), KS3 contains COM as a major mineral phase. For long τ , sharp lines
230 (associated to mobile components) were obtained whereas the broader COM component around 5.2 ppm was totally suppressed.
 $\delta_{\text{iso}}(^1\text{H})$ values agree with unsaturated fatty acids ($\delta_{\text{iso}}(^1\text{H}) \sim 5.25$ ppm) (Ren et al., 2008). The presence of triglycerides is
excluded as the CH and CH_2 resonances of the glycerol backbone ($\delta_{\text{iso}}(^1\text{H}) \sim 5.0$ and 4.0 ppm, respectively) were not detected.

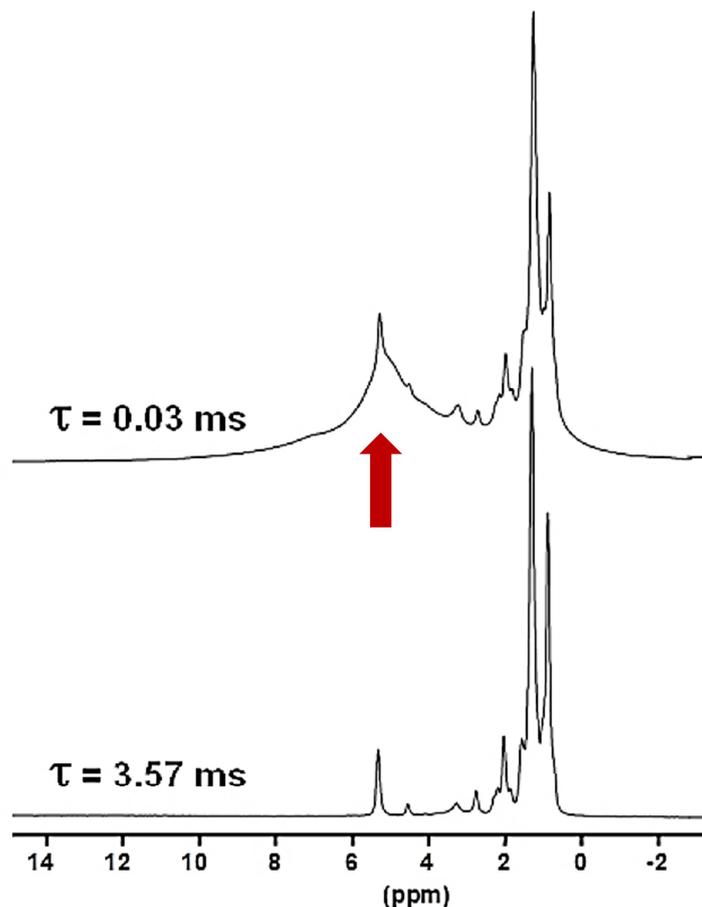


235 **Figure 4.** ^1H Hahn echo MAS NMR spectra for KS3 recorded at 16.4 T. τ was synchronized with the rotation frequency, here $\nu_{\text{rot}} = 30$ kHz. No temperature control was implemented leading to a ~ 40 °C increase of the sample temperature and the associated increase of local dynamics. The vertical red arrow corresponds to the resonance coming from COM (see also Figures 1a and 1b).

240 Such level of resolution allowed for the implementation of J-MAS derived pulse schemes such as the ^1H - ^1H DQF COSY MAS experiment (based on isotropic $J(^1\text{H}-^1\text{H})$ couplings). This experiment is part of the toolbox for more general dynamics-based spectral editing research topic, applied to biological solids (Mroue et al., 2016; Matlahov and van der Wel, 2018; Gopinath and Veglia, 2018). The ^1H - ^1H DQF COSY MAS spectrum is presented in Figure 5a for KS3. All resonances of the mobile fatty acid chains were assigned in a straightforward way demonstrating the pertinence of this *through bond* correlation
245 experiment. On the other hand, dipolar based double quantum (DQ) experiments can be implemented to establish *through space* proximities between protons (such as BABA, Back to Back) (Feike et al., 1996). It is a distinct advantage to perform such experiments under very-fast MAS (here 79 kHz). Indeed, the spectral resolution is drastically increased leading to an



easier observation of the correlation peaks. The ^1H - ^1H DQ BABA MAS NMR spectrum of KS3 is presented in Figure 5b. The ^1H resonance corresponding to the COM phase is clearly evidenced on the ^1H projection and on the 2D diagonal (red arrows).
250 Moreover, red dashed ovals indicate correlations involving the protons of the immobile proteins contained in KS3 (essentially the $^1\text{H}^{\text{N}}-^1\text{H}^{\alpha}$, $^1\text{H}^{\alpha}-^1\text{H}^{\beta}$ regions). ^1H spin diffusion experiments should help to highlight actual correlations between the organic and inorganic components, at the interface (Schmidt-Rohr and Spiess, 1994).

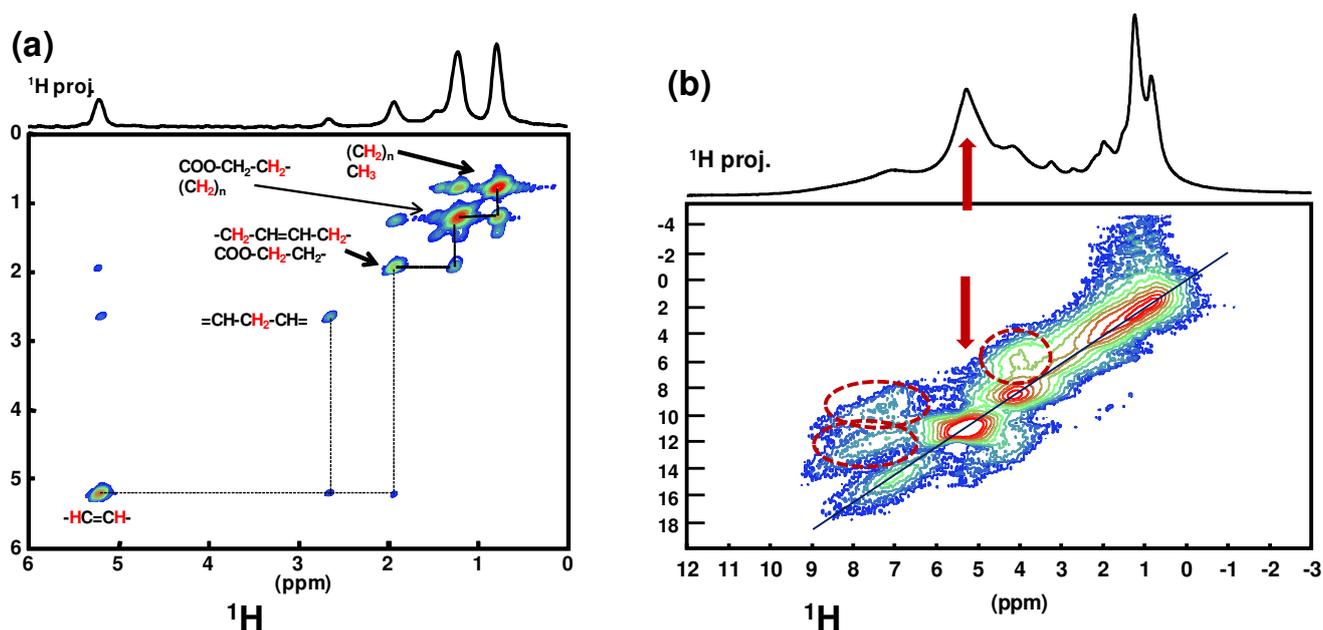

255 **Figure 5.** (a) ^1H - ^1H DQF COSY MAS NMR spectrum for KS3 at $\nu_{\text{rot}} = 30$ kHz recorded at 16.4 T. Here, no temperature control was implemented leading to an ~ 40 °C increase of the local temperature and therefore of local dynamics. All peaks are assigned to contributions from unsaturated mobile fatty acids (with unsaturations). (b) ^1H - ^1H DQ BABA MAS NMR spectrum for KS3 at $\nu_{\text{rot}} = 79$ kHz recorded at 16.4 T (no temperature control). Recoupling period: 2 rotor periods. Off-diagonal correlations (immobile organic moieties) are highlighted by dashed red ovals. The red arrows indicate the COM contribution.

260 3 Natural abundance ^{43}Ca solid state NMR experiments

Natural abundance solid state ^{43}Ca MAS NMR spectroscopy remains a challenge. Indeed, the NMR characteristics of this quadrupolar nucleus ($I = 7/2$) are clearly unfavourable: natural abundance: 0.14 % and low γ ($\nu_0 = 57.2$ MHz at 20 T). Nevertheless four main experimental approaches have been successfully developed during the last few years: (i) using large volume rotors (7 mm, ~ 400 mg of sample) at high magnetic field (20 T), under moderate MAS (~ 5 kHz) and implementing
265 DFS (Double Frequency Sweep) excitation scheme (section 7), (ii) using much smaller rotors (3.2 mm, ~ 20 mg of sample at



ultra-high magnetic field (35.2 T) and under moderate/fast MAS (~ 18 kHz), (iii) using Dynamic Nuclear Polarization (DNP) to strongly enhance the ^{43}Ca polarization, usually in the indirect mode (from ^1H to ^{43}Ca), (iv) labeling in ^{43}Ca (starting from an enriched calcite precursor) (Laurencin et al., 2021; Smith, 2020; Laurencin and Smith, 2013). Here, we follow the approach (i) which is by far the easiest to implement in most NMR facilities worldwide (as long as a low- γ probe is available).

270 The first contributions related to the study of synthetic calcium oxalates hydrates by ^{43}Ca MAS NMR spectroscopy were proposed by Wong for COT (Wong et al., 2006) and by Bowers and Kirkpatrick for the three hydrated phases (Bowers and Kirkpatrick, 2011). The latter claimed that the COM lineshape could be attributed to an averaged Gaussian signal due to a local disorder in the structure (Tazzoli and Domeneghetti, 1980). Colas (Colas et al., 2013) demonstrated that high signal-to-noise ratio is necessary to extract reliable quadrupolar parameters from natural abundance ^{43}Ca MAS NMR spectra

275 and re-investigated the COM phase. Instead of a Gaussian contribution, two distinct resonances were evidenced, in agreement with the crystallographic data ($\delta_{\text{iso}}(^{43}\text{Ca}) = -2.6$ ppm, $C_Q = 1.50$ MHz, $\eta_Q = 0.60$; $\delta_{\text{iso}}(^{43}\text{Ca}) = 0.7$ ppm, $C_Q = 1.60$ MHz, $\eta_Q = 0.70$). The ^{43}Ca MAS NMR spectra of COM, COD and COT recorded at 20.0 T are presented in Figure 6a. All spectra were obtained in natural abundance in a reasonable amount of experimental time (~ 2 hours for COM and COT, ~ 4 hours for COD). The ^{43}Ca NMR fingerprints obtained allows unambiguous distinctions of the three phases. The sharpest line

280 (characterized by the smallest C_Q) is observed for COT (one unique crystallographic site). For this particular phase, second-order quadrupolar broadening is efficiently suppressed at 20 T, leading directly to $\delta_{\text{iso}}(^{43}\text{Ca}) = -0.1$ ppm. This value is slightly different from the one reported by Wong (*i.e.* -4.2 ppm) (Wong et al., 2006). Such a discrepancy can be attributed to a difference in chemical shift referencing (Gervais et al., 2008). The associated quadrupolar parameters for COT (Wong et al., 2006) were $C_Q = 1.55$ MHz, $\eta_Q = 0.72$. C_Q is probably overestimated as such value would definitely produce second-order

285 quadrupolar broadening under MAS at 20.0 T (see above the quadrupolar parameters for COM). Finally, a rather featureless spectrum is obtained for COD (one crystallographic site), exhibiting a much larger linewidth than for COT ($\delta_{\text{iso}}(^{43}\text{Ca}) \sim -2.6$ ppm, $C_Q \sim 1.60$ MHz, $\eta_Q \sim 0.20$). We assign this broadening to the distribution of *zeolitic* water molecules (leading consequently to a slight distribution of $\delta_{\text{iso}}(^{43}\text{Ca})$). Hence, it is demonstrated that natural abundance ^{43}Ca MAS NMR spectroscopy is useful in characterizing hydrated calcium oxalate phases. The use of moderate MAS is sufficient to retrieve

290 satisfactory resolution as characteristic $C_Q(^{43}\text{Ca})$ are usually small/very small (< 1.8 MHz). However, the $\delta_{\text{iso}}(^{43}\text{Ca})$ range covered by these three phases is small making this NMR parameter less sensitive distinguishing the hydrates. This comes from the fact that $\delta_{\text{iso}}(^{43}\text{Ca})$ is mainly determined by the coordination of the Ca atoms and the mean $\langle \text{Ca-O} \rangle$ distances. These parameters are almost identical for COM, COD and COT (8-fold coordination for COM and COD, 7-fold coordination for COT, range of averaged Ca–O distances: 2.47–2.49 Å. This last comment is rather in contradiction with previous conclusions

295 proposed in the literature (Bowers and Kirkpatrick, 2011).

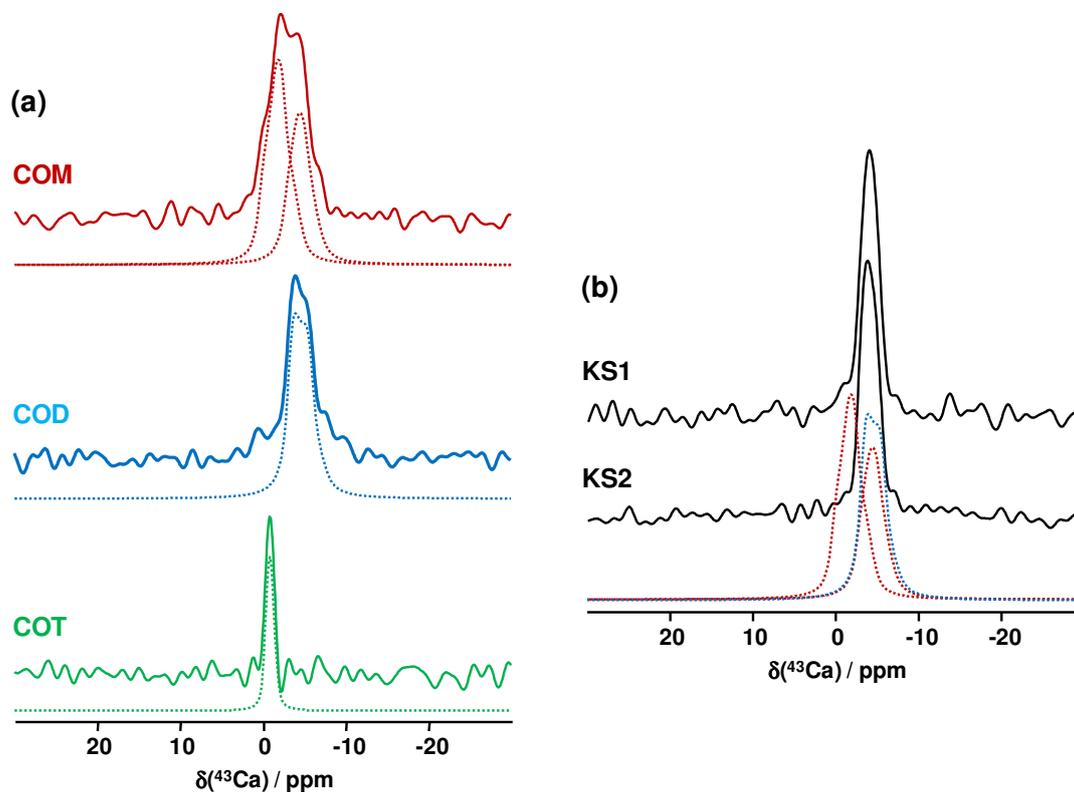


Figure 6. (a) Natural abundance ^{43}Ca MAS NMR spectra of COM (red), COD (blue) and COT (green) recorded at 20.0 T ($v_{\text{rot}} = 3$ to 5 kHz). The dashed lines correspond to fits. (b) Natural abundance ^{43}Ca MAS NMR spectra of KS1 and KS2. The red dashed lines correspond to the two resonances associated to COM. The blue dashed line corresponds to the ^{43}Ca MAS NMR spectrum of COD.

The natural abundance ^{43}Ca MAS NMR spectra of KS1 and KS2 are presented in Figure 6b. They are largely similar to the COD spectrum overall. The contribution of a COM component is hardly discernable (though present, especially in KS1, see Figure 7). As stated above, the structure of COM is subject to subtle structural variations which could lead to the overlap of the two ^{43}Ca resonances. In other words, though interesting in principle, natural abundance ^{43}Ca MAS NMR spectroscopy (associated inherently to limited signal-to-noise ratio) should not be used as a first solid state NMR tool of investigation for KS.

4 Back to ^{13}C NMR: spectral edition and reconstruction of spectra

^{13}C NMR data related to synthetic calcium oxalate phases and KS are the most represented in the literature. This is probably due to the fact that the spectral resolution is high under MAS and that CP (cross polarization) MAS experiments can easily be

implemented even at low or moderate magnetic field. Typical ^{13}C CP MAS NMR spectra for COM and COD are presented in Figure 7 (bottom). Four isotropic resonances are observed for COM as expected from XRD data (Colas et al., 2013) and one unique broader resonance is observed for COD as expected from XRD data considering the disorder associated to the *zeolitic* water molecules. Such disorder has an impact on the resolution of the ^{13}C NMR spectra.

315


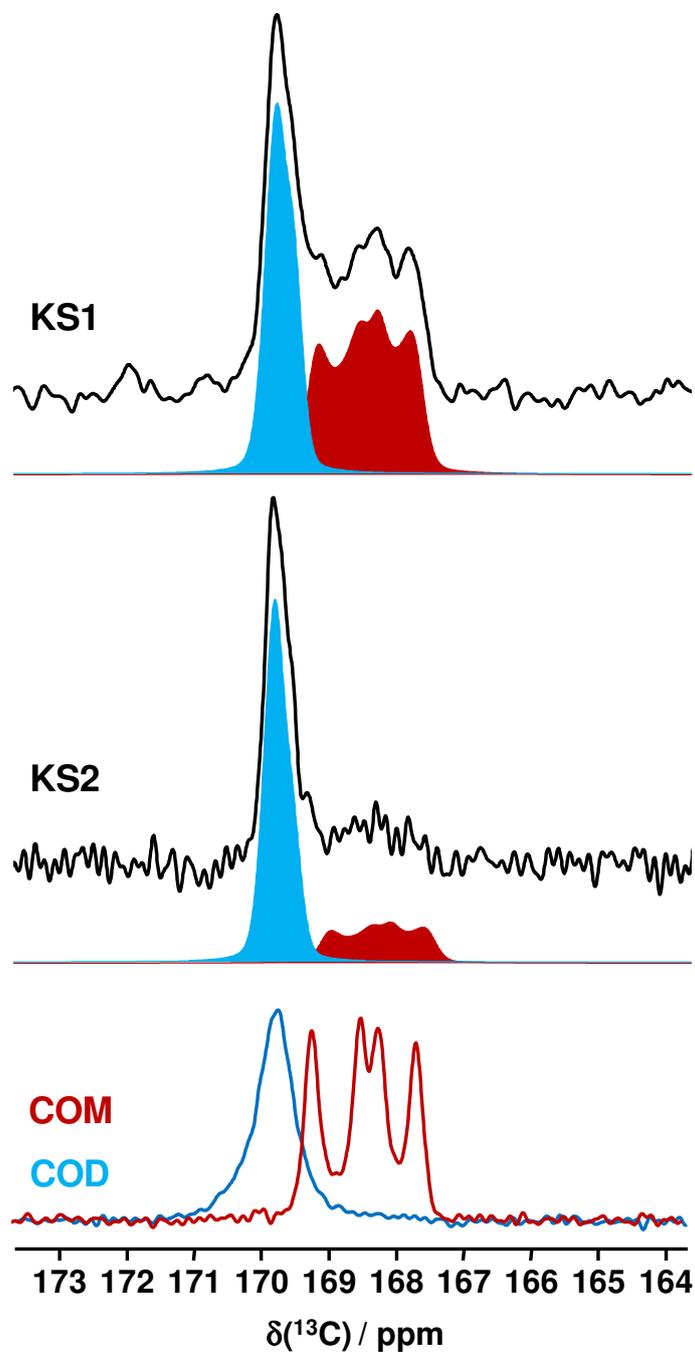


Figure 7. ^{13}C CP MAS NMR spectra of KS1 and KS2 (recorded at 16.4 T, $\nu_{\text{rot}} = 5$ kHz) and the corresponding COM (red) and COD (blue) contributions. Bottom: ^{13}C CP MAS NMR spectra of synthetic COM (red line) and COD (blue line) recorded under similar conditions.



It is observed that the chemical shift range of interest is very restricted (~ 4 ppm from 167 to 171 ppm) corresponding to ~ 0.8% of the whole ^{13}C isotropic chemical shift range. ^{13}C CP MAS NMR spectra for KS1 and KS2 are also presented in Figure 7. The presence of COM and COD components is clearly evidenced and could be quantified if necessary (by increasing the signal-to-noise ratio significantly). As a matter of fact, a single experiment at fixed contact time (usually > 5 ms) is sufficient in principle for quantitative purposes as ^1H - ^{13}C dipolar couplings are comparable for all ^{13}C sites (differences in relative intensities can be evidenced at much short contact time, *i.e.* < 0.5 ms). The case of KS3 is by far more complex. As stated in section 1, a given KS may include a complex organic component, containing lipids, triglycerides, membrane components, glycoproteins (like the Tamm-Horsfall protein) and glycoaminoglycans, among other species (Reid et al., 2011). The approximate chemical composition of KS3 is: ~ 10 % proteins, ~ 20-25 % COM and ~ 65 % amorphous silica (Dessombz et al., 2016). In Figure 8, we propose a robust protocol to reconstruct the ^{13}C MAS NMR spectra starting from well identified sub-spectra. At short contact time (0.8 ms), all carbon-containing species are detected, corresponding to both sharp and broad lines (Figure 8a).

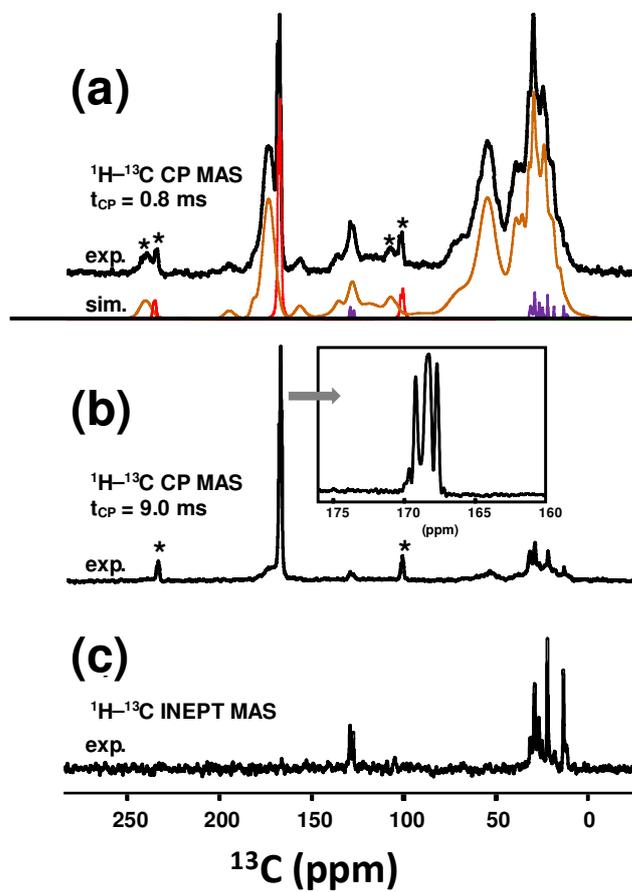

335



Figure 8. (a) ^{13}C CP MAS NMR spectrum of KS3 (recorded at 7.0 T using a short contact time, 0.8 ms, $\nu_{\text{rot}} = 5$ kHz). The experimental spectrum is decomposed in three components: COM (in red), fatty acids (in purple) and proteins (in brown). (b) ^{13}C CP MAS NMR spectrum of KS3 (recorded at 7.0 T using a long contact time, 9.0 ms). The insert highlights the COM contribution (four resonances, two of them being almost overlapped) (Colas et al. 2013). (c) ^1H - ^{13}C refocused INEPT J-MAS
340 NMR spectrum of KS3 (recorded at 7.0 T). The unsaturations of the fatty acids are clearly evidenced at $\delta_{\text{iso}}(^{13}\text{C}) \sim 130$ ppm.
*: spinning sidebands.

Then, a $T_{1\rho}(^1\text{H})$ filter was applied by increasing the contact time by a factor of ~ 10 leading to the drastic reduction of the intensities of the broad components. The four resonances of COM are clearly observed (insert in Figure 8b). COD is absent in
345 agreement with powder XRD and FTIR data. It follows that the proton spin baths corresponding to COM and the broad
components are independent (spin diffusion and domain size measurements could be implemented as complementary experiments (Schmidt-Rohr and Spiess, 1994). The 1D ^1H - ^{13}C refocused INEPT J-MAS NMR sequence (Figure 8c) allowed selective extraction of the mobile components corresponding to the fatty acids (see also Figure 5a). The unsaturated nature is clearly evidenced by the shift at $\delta_{\text{iso}}(^{13}\text{C}) \sim 130$ ppm. Finally, the ^{13}C CP MAS NMR spectrum (Figure 8a, bottom) could be reconstructed with resonances from: (i) the COM phase and its associated spinning sidebands (in red), (ii) fatty acids
350 characterized by very sharp lines (in purple), (iii) and proteins (in brown) (Cavanagh et al., 2007) for which a precise attribution cannot be given at this stage.

5 The ubiquitous (but elusive) presence of phosphorus in KS: ^{31}P MAS and CP MAS experiments

Bak *et al.* (Bak et al., 2000) used ^{31}P MAS and CP MAS experiments to evidence phosphate-containing phases in KS. The presence of phosphate groups in KS is not unusual and observed mainly by FTIR (Figure S1). However, their exact chemical
355 nature remains unclear. Phosphates in KS can correspond to: (i) mineral phases such as substituted (carbonated) hydroxyapatite ($\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$), brushite ($\text{CaHPO}_4 \cdot 2\text{H}_2\text{O}$) or struvite ($\text{NH}_4\text{MgPO}_4 \cdot 6\text{H}_2\text{O}$), (ii) organic phosphates present in phospholipids (in the cell membrane) and/or DNA, RNA, ATP molecules (Butusov and Jernelöv, 2013). Usually, phosphates are found as minor components in KS making ^{31}P NMR attractive given the high inherent signal sensitivity of ^{31}P (which is also an $I = 1/2$ nucleus). A total of six KS (exhibiting COM as the major phase and the "apparent" absence of phosphate phases by powder
360 XRD) were studied here. The representative ^{31}P MAS and CP MAS NMR spectra of the KS are presented in Figure 9.

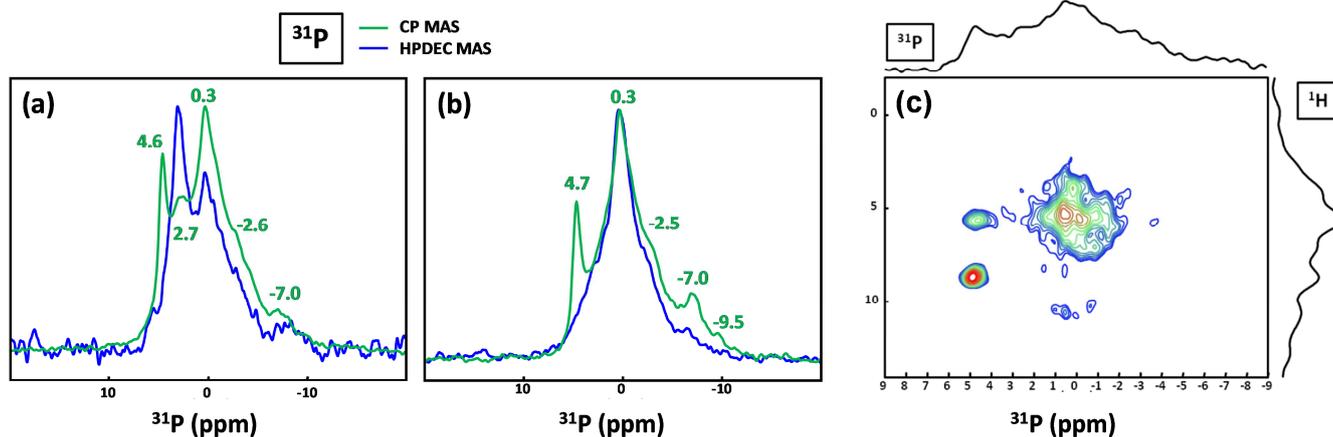


Figure 9. (a) ^{31}P MAS under high power $\{^1\text{H}\}$ decoupling (in blue) and CP MAS (in green) NMR spectra of KS4. Some
365 specific chemical shifts are highlighted. (b) ^{31}P MAS under high power $\{^1\text{H}\}$ decoupling (in blue) and CP MAS (in green)
NMR spectra of KS5 (representative of an ensemble of five KS). Some specific chemical shifts are highlighted. (c) ^1H - ^{31}P
HETCOR CP MAS NMR spectrum of KS4 (temperature control at -20°C). All spectra shown here were recorded at 16.4 T.

The ^{31}P NMR fingerprint of KS4 is specific (Figure 9a), whereas KS5 has a ^{31}P fingerprint analogous to four other KS (Figure
370 9b). The acquisition time is ~ 2 to 3 hours demonstrating that the amount of phosphate species is indeed small in all samples.
One notes a large distribution of $\delta_{\text{iso}}(^{31}\text{P})$, corresponding not only to structural disorder, but also to strong chemical variability.
In order to facilitate the assignment of $\delta_{\text{iso}}(^{31}\text{P})$, ^1H - ^{31}P HETCOR CP MAS NMR experiments under active temperature control
($T = -20^\circ\text{C}$) were implemented as well (Figure 9c). Three clear correlations were observed: $\delta_{\text{iso}}(^{31}\text{P}) = 4.6 \text{ ppm} \leftrightarrow \delta_{\text{iso}}(^1\text{H}) =$
375 8.7 ppm ; $\delta_{\text{iso}}(^{31}\text{P}) = 4.6 \text{ ppm} \leftrightarrow \delta_{\text{iso}}(^1\text{H}) = 5.7 \text{ ppm}$, $\delta_{\text{iso}}(^{31}\text{P}) \sim 0.25\text{-}0.30 \text{ ppm} \leftrightarrow \delta_{\text{iso}}(^1\text{H}) = \sim 5.0 \text{ ppm}$. Reasonable assignments
are the following (Godinot et al., 2016): (i) The peak centered at $\delta_{\text{iso}}(^{31}\text{P}) = 4.6 \text{ ppm}$ is assigned to struvite, $\text{NH}_4\text{MgPO}_4 \cdot 6\text{H}_2\text{O}$
(Bak et al., 2000). The correlation centred at $\delta_{\text{iso}}(^{31}\text{P}) = 4.6 \text{ ppm} \leftrightarrow \delta_{\text{iso}}(^1\text{H}) = 8.7 \text{ ppm}$ (ammonium groups) is attributed to
 $\text{PO}_4^{3-}/\text{NH}_4^+$. The correlation centred at $\delta_{\text{iso}}(^{31}\text{P}) = 4.6 \text{ ppm} \leftrightarrow \delta_{\text{iso}}(^1\text{H}) = 5.7 \text{ ppm}$ concerns water molecules. It is interesting to
note that the amount of struvite is extremely small (almost absent in the ^{31}P MAS NMR spectrum of KS4 and KS5 - Figures
9a and 9b). (ii) The resonance at $\delta_{\text{iso}}(^{31}\text{P}) = 0.3 \text{ ppm}$ may be attributed to phosphates in phospholipids (in this case $\delta_{\text{iso}}(^{31}\text{P})$ is
380 in the ~ 1 to -1 ppm range). However, correlations with $\delta_{\text{iso}}(^1\text{H}) < 3 \text{ ppm}$ are almost absent (such resonances should be
characteristic for long alkyl chains in phospholipids). Consequently, we assign the ^{31}P resonance to inorganic (hydrated)
orthophosphates. (iii) $\delta_{\text{iso}}(^{31}\text{P}) \sim 2.7 \text{ ppm}$ could be potentially assigned to amorphous calcium phosphate with a rather small
(rather unusual) level of protonation (this resonance is underestimated in the CP MAS experiment, Figure 9a). (iv) $\delta_{\text{iso}}(^{31}\text{P}) \ll 0 \text{ ppm}$ resonances are assigned to pyro- and/or polyphosphates.



385 6 Conclusions and perspectives

This study has demonstrated that the solid state NMR technique offers a complementary characterisation approach for the study of kidney stones and related synthetic model systems. The ^1H DUMBO MAS NMR technique provides unambiguous identification of the different calcium oxalate hydrate phases. This experiment is a rapid-measurement technique which can be easily adapted to yield semi-quantitative data. For the first time, the natural abundance ^{43}Ca MAS NMR data from the three
390 calcium oxalate hydrate phases have been presented together; these data exhibited sufficient signal-to-noise to facilitate a complete structural interpretation in agreement with crystallographic data. The extension of this approach to the study of KS was attempted showing that a real signal could be measured, but with relatively limited discrimination between the different KS samples. The deconvolution of the ^1H and ^{13}C MAS NMR data into assigned sub-spectra aided the interpretation of the
395 data describing the whole system, thus demonstrating that KS materials are usually a complex association of organic and inorganic components. Additional ^{31}P MAS NMR studies provided further insight into the composition of the low-level phosphates which are ubiquitous and difficult to characterize in KS. The development of solid state NMR, in combination with modern computational DFT and Machine Learning approaches, would be able to characterize the complex heterogeneous biomaterials such as KS without ambiguity (Tielens et al., 2021). As part of on-going studies building on the observations
400 here, systematic NMR studies of a large range of KS from the Tenon Hospital's collection is being undertaken to develop new diagnosis NMR approaches that could impact on developing novel treatments.

7 Syntheses of hydrated calcium oxalate, kidney stones samples and NMR methods

Synthesis. Calcium chloride (CaCl_2) and sodium oxalate ($\text{Na}_2\text{C}_2\text{O}_4$) were purchased from Sigma-Aldrich and used as received. All syntheses were carried out using distilled water. COM: at 40°C , equimolar aqueous solutions of $\text{Na}_2\text{C}_2\text{O}_4$ and CaCl_2
405 (0.1 mol.L^{-1}) were added simultaneously dropwise in a few mL of water under magnetic stirring. The mixture was left mixing under these conditions during 2 hours before filtration and was then washed with cold water before drying under air. COD: a $\text{Na}_2\text{C}_2\text{O}_4$ aqueous solution (0.1 mol.L^{-1}) and a CaCl_2 solution (1.0 mol.L^{-1} , $\text{Ca/Ox} = 10$) were prepared the day prior to the reaction and stored between $2\text{--}6^\circ\text{C}$ overnight. The solution of $\text{Na}_2\text{C}_2\text{O}_4$ was added dropwise to the CaCl_2 solution in an ice bath ($T < 7^\circ\text{C}$) under magnetic stirring. The mixture was left under stirring for 15 min before filtration and was then washed
410 with cold water before drying under air. COT: in an ice bath, two equimolar (0.001 mol.L^{-1}) aqueous solutions of $\text{Na}_2\text{C}_2\text{O}_4$ and CaCl_2 were slowly added simultaneously dropwise in a few mL of water under vigorous magnetic stirring. The mixture was left under stirring for 15 min before filtration and was then washed with cold water before drying under air. All COM, COD, COT samples were obtained as white fine powders. COD and COT were rapidly stored between $2\text{--}6^\circ\text{C}$ while COM could be stored at ambient temperature. *Kidney stones.* The samples were provided by Dr M Daudon (Tenon Hospital, Paris,
415 France). The choice of the diameter of the used NMR rotor was dictated by the initial size of the KS and the implemented



experiments. In the case of large KS, smaller pieces were studied as powders by NMR. *NMR methods. Warning:* the COM structure is highly sensitive to temperature variations (≥ 15 °C). The lowest MAS frequencies have to be implemented for all investigated nuclei as well as active regulation of the sample temperature (Bruker BCUX unit). Most of the ^1H MAS and DUMBO MAS NMR spectra presented in Figure 1 were obtained at 700 MHz (Bruker AVANCE III spectrometer) using a
420 2.5 mm Bruker MAS probe spinning the sample at 12 kHz (number of scans: 20 to 40, recycle delay: 10 s for quantitative measurements, temperature: 10 °C, $t_{90^\circ}(^1\text{H}) = 3.0$ μs , duration of the shape length: 24 μs at 113 kHz RF field). The DUMBO experiment was first set up with glycine as a test sample (including the scaling of the isotropic chemical shift) and then optimized for each compound. Some ^1H MAS NMR spectra were obtained at 850 MHz using a 1 mm JEOL MAS probe (spinning the sample up to 79 kHz) (number of scans: 4, recycle delay: 3 s, $t_{90^\circ}(^1\text{H}) = 1.70$ μs). Synchronized Hahn echoes
425 (Figure 4) were performed at 700 MHz using a 2.5 mm Bruker MAS probe spinning the sample at 30 kHz (number of scans: 64, recycle delay: 5 s, $t_{90^\circ}(^1\text{H}) = 2.8$ μs , no active regulation of the temperature in order to increase local dynamics – the increase in temperature is estimated to ~ 40 °C). The ^1H – ^1H DQF COSY MAS NMR experiment (Figure 5) was performed at 700 MHz using a 2.5 mm Bruker MAS probe at 30 kHz (number of scans: 32, recycle delay: 2 s, $t_{90^\circ}(^1\text{H}) = 2.8$ μs , 256 increments in t_1 dimension, no active regulation of the temperature in order to increase local dynamics, magnitude mode). The ^1H – ^1H SQ-DQ
430 BABA MAS NMR experiment (Figure 5) was performed at 850 MHz using a 1 mm JEOL MAS NMR probe spinning the sample at 79 kHz (number of scans: 16, recycle delay: 3 s, $t_{90^\circ}(^1\text{H}) = 1.70$ μs , 2 BABA loops, 426 increments in t_1 dimension, no active regulation of the temperature). All ^1H NMR spectra were referenced using adamantane (1.85 ppm) as a secondary reference. All natural abundance ^{43}Ca NMR spectra (Figure 6) were obtained at 850 MHz (Bruker AVANCE III spectrometer) using a 7 mm low- γ Bruker MAS single channel NMR probe spinning the sample at 3 to 5 kHz. A DFS (Double Frequency
435 Sweep) (Iuga et al., 2000) enhancement scheme followed by a 90° selective pulse of 1.5 μs , was used (DFS pulse length of 2 ms, RF ~ 8 kHz, and convergence sweep from 400 to 50 kHz, number of scans: from 5600 to 18000, recycle delay: 0.8 s). All ^{43}Ca chemical shifts were referenced at 0.0 ppm to a 1.0 mol.L $^{-1}$ aqueous solution of CaCl_2 (Gervais et al., 2008). The ^1H – ^{13}C RAMP CP MAS experiments (Figure 7) were obtained at 700 MHz (Bruker AVANCE III spectrometer) using a 2.5 mm Bruker MAS double resonance NMR probe spinning the sample at 5 kHz (number of scans: 600 to 1200, recycle delay: 3 s,
440 $t_{90^\circ}(^1\text{H}) = 3.1$ μs , contact time: 2 to 8 ms). The ^{13}C MAS NMR spectra presented in Figure 8 were obtained at 300 MHz (Bruker AVANCE III spectrometer) using a 7 mm Bruker MAS double resonance NMR probe spinning the sample at 5 kHz (number of scans: 328, recycle delay: 3 s, $t_{90^\circ}(^1\text{H}) = 5.2$ μs , contact time: 0.8 and 9.0 ms, refocused INEPT MAS: number of scans: 6000, recycle delay: 3 s, 5.2 and 3.2 μs $\pi/2$ pulse on ^1H and ^{13}C respectively, no active regulation of the temperature). All ^{13}C NMR spectra were referenced using adamantane (38.48 ppm) as a secondary reference. ^{31}P 1D and 2D NMR spectra
445 presented in Figure 9 were obtained at 700 MHz (Bruker AVANCE III spectrometer) using a 2.5 mm Bruker MAS double resonance NMR probe spinning the sample at 30 kHz (number of scans: ≈ 4000 for high power $\{^1\text{H}\}$ decoupling experiments and ≈ 3700 for CP MAS experiments, recycle delay: 10 s for high power $\{^1\text{H}\}$ decoupling experiments and flip angle: 30° , 3 s for CP MAS experiments, $t_{90^\circ}(^1\text{H}) = 2.0$ μs , contact time for CP MAS experiments: 5.0 ms). For the ^1H – ^{31}P HETCOR RAMP



CP MAS experiment: number of scans: 400, recycle delay: 3 s, $t_{90}({}^1\text{H}) = 2.0 \mu\text{s}$, contact time: 5.0 ms, 96 increments in t_1
450 dimension, active regulation of the temperature at $-20 \text{ }^\circ\text{C}$.

Relaxation of crystallographic structures. Starting from the crystallographic data, COM (Daudon et al., 2009), COD (Tazzoli
and Domeneghetti, 1980) and COT (Basso et al., 1997) structures were relaxed at DFT level. The unit cell parameters as well
as the atomic positions were optimized as previously described for COM (Colas et al., 2013). VASP was used (Kresse and
Hafner, 1993; Kresse and Hafner, 1994; Kresse and Furthmüller, 1996). The corresponding CIF files are available upon
455 request.

8 Appendices

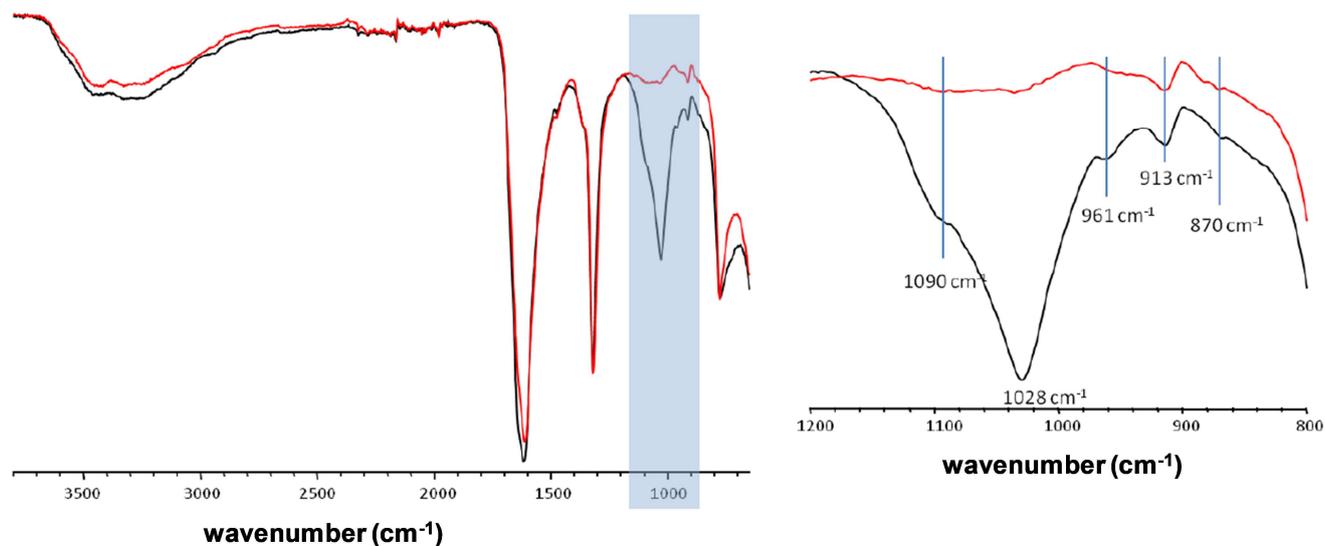


Figure A1. FTIR spectra of two KS containing a mixture of COM and COD phases. The main difference lies in the light blue
460 wavenumber region corresponding to phosphate vibrations (including hydroxyapatite: 913, 961, 1090 cm^{-1} , carbonates:
870 cm^{-1}).

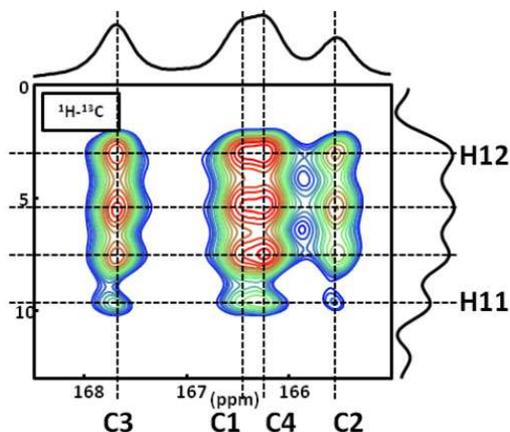


Figure A2. ^1H - ^{13}C CP DNP MAS NMR spectrum of COM at $T = 100$ K. Four distinct ^1H resonances are clearly evidenced on the ^1H indirect dimension. The contact time is 9.0 ms and sixteen $^1\text{H}/^{13}\text{C}$ correlations are observed.

465

Table A1. All CIF files are available upon request for COM, COD and COT.

(a) selected O-H...O distances and number of H...O contacts with $\text{O-H}\dots\text{O} \leq 3\text{\AA}$ (highlighted in yellow) for COM. The atomic positions were optimized at the DFT level.

H11	O100	1.00849	H12	O100	0.98369	H21	O200	0.99077	H22	O200	0.98971
H11	H12	1.57350	H12	H11	1.57350	H21	H22	1.60332	H22	H21	1.60332
H11	O8	1.64743	H12	O5	1.95727	H21	O5	1.75421	H22	O100	1.84259
H11	C4	2.32231	H12	H22	2.34911	H21	C3	2.41467	H22	H12	2.34911
H11	H22	2.38986	H12	C3	2.43432	H21	O6	2.59359	H22	H11	2.38986
H11	O7	2.54004	H12	O1	2.82575	H21	Ca1	2.91456			
H11	Ca2	2.97148	H12	Ca2	2.90392	H21	H12	2.92563			
			H12	H21	2.92563						
			H12	O8	2.97218						

470 (b) selected O-H...O distances and number of H...O contacts with $\text{O-H}\dots\text{O} \leq 3\text{\AA}$ (highlighted in yellow) for COD. The atomic positions were optimized at the DFT level. In order to take into account the distribution of the *zeolitic* water molecules, a model corresponding to $\text{CaC}_2\text{O}_4 \cdot (2+0.375)\text{H}_2\text{O}$ was first calculated (see below) - $\text{Ca}_8\text{C}_{16}\text{O}_{32}(\text{H}_2\text{O})_{16}(\text{H}_2\text{O})_3$. The water molecules located in the channels of the *zeolitic* structure are represented in *italics*. The "less rigid" molecules are highlighted in red rectangles. The first 4 molecules are structural. The last 3 molecules are *zeolitic*.




H1	O33	0.98706	H2	O34	0.98980	H3	O34	0.98182	H4	O33	0.99442	H5	O35	0.98170	H6	O36	0.98695	H7	O36	0.98579
H1	H4	1.55955	H2	H3	1.57549	H3	H2	1.57549	H4	H1	1.59565	H5	H8	1.61227	H6	H7	1.58205	H7	H6	1.58205
H1	O26	1.91539	H2	O25	1.82678	H3	O28	2.04985	H4	O27	1.75128	H5	O30	1.85900	H6	O29	1.87561	H7	O32	1.91645
H1	H17	2.11120	H2	H18	2.12287	H3	H2	2.22917	H4	H38	1.97874	H5	H21	2.15627	H6	H22	2.14944	H7	H23	2.15003
H1	H38	2.35789	H2	H37	2.24223	H3	H37	2.66372	H4	H20	2.04373	H5	O14	2.75907	H6	H37	2.31981	H7	H22	2.69686
H1	H20	2.69799	H2	H19	2.67477	H3	H18	2.70041	H4	H17	2.52979	H5	C10	2.81281	H6	H23	2.64503	H7	O16	2.78683
H1	O44	2.73922	H2	H8	2.74763	H3	O12	2.81150	H4	O44	2.63337	H5	H24	2.83299	H6	O42	2.77692	H7	O42	2.79486
H1	O10	2.79429	H2	O9	2.75952	H3	O43	2.84290	H4	C13	2.86844	H5	O41	2.88697	H6	O13	2.79229	H7	H37	2.91901
H1	C16	2.86355	H2	C15	2.77043	H3	H8	2.86354	H4	O11	2.84953	H5	Ca3	2.93317	H6	C9	2.81462	H7	C12	2.85808
H1	Ca1	2.99269	H2	O43	2.77691	H3	C14	2.95471	H4	O51	2.90084	H5			H6	Ca4	2.92805	H7	Ca4	2.95463
			H2	O51	2.78975	H3	Ca2	2.98530	H4	O4	2.93927	H5			H6	O6	2.99753	H7		
			H2	Ca2	2.93267	H3			H4	Ca1	2.96741	H5			H6			H7		
H8	O35	1.00238	H9	O37	0.98455	H10	O38	0.98386	H11	O38	0.98764	H12	O37	0.98525	H13	O39	0.98603	H14	O40	0.98212
H8	O51	1.66198	H9	O18	1.89267	H10	O17	1.85718	H11	O50	1.85667	H12	O19	1.84639	H13	O50	1.83852	H14	O21	2.13357
H8	H38	1.99179	H9	H25	2.14908	H10	H26	2.12211	H11	H36	2.17741	H12	H28	2.07478	H13	H36	2.35234	H14	H30	2.23119
H8	H37	2.04976	H9	H36	2.36458	H10	H33	2.34664	H11	H13	2.40635	H12	H34	2.50717	H13	H11	2.40635	H14	H31	2.65940
H8	H2	2.74763	H9	H28	2.64453	H10	H27	2.65917	H11	H35	2.60426	H12	H25	2.62744	H13	H35	2.56253	H14	H31	2.70447
H8	O15	2.84946	H9	O48	2.77037	H10	O47	2.76488	H11	O20	2.76299	H12	O48	2.71565	H13	O22	2.81506	H14	O5	2.79807
H8	H3	2.86354	H9	O2	2.78591	H10	C7	2.80358	H11	O39	2.81858	H12	O3	2.76892	H13	H29	2.85749	H14	O46	2.83725
H8	H24	2.93412	H9	Ca	2.86976	H10	O1	2.88960	H11	O4	2.82351	H12	C5	2.83943	H13	O6	2.93190	H14	O38	2.89969
H8	O31	2.96498	H9	Ca5	2.93707	H10	O39	2.92353	H11	H27	2.85030	H12	Ca5	2.95153	H13			H14	H33	2.94527
H8	O34	2.99827	H9	O50	2.98631	H10	Ca6	2.98407	H11			H12	H36	2.99920	H13			H14		
H15	O40	0.99513	H16	O39	0.98321	H17	O44	0.98418	H18	O43	0.98306	H19	O43	0.98845	H20	O44	0.98141	H21	O41	0.98524
H15	H14	1.57384	H16	H13	1.60309	H17	H20	1.58638	H18	H19	1.58312	H19	H18	1.58312	H20	H17	1.58638	H21	H24	1.59032
H15	O24	1.77827	H16	O23	1.89139	H17	O26	1.88650	H18	O25	1.90254	H19	O28	1.85208	H20	O27	1.97101	H21	O30	1.84549
H15	H31	2.12464	H16	H32	2.16066	H17	H1	2.11120	H18	H2	2.12287	H19	H3	2.22917	H20	H4	2.04373	H21	H5	2.15627
H15	H36	2.19988	H16	H29	2.69091	H17	C16	2.50781	H18	C15	2.52659	H19	C14	2.48695	H20	C13	2.60434	H21	C10	2.45627
H15	H30	2.67389	H16	C3	2.79378	H17	H4	2.52979	H18	H3	2.70041	H19	H2	2.67477	H20	H1	2.69799	H21	C10	2.45627
H15	Ca	2.70528	H16	O45	2.80838	H17	O33	2.71797	H18	O34	2.78743	H19	O34	2.82331	H20	O33	2.77138	H21	O35	2.74039
H15	O8	2.75027	H16	O7	2.82588	H17	O1	2.96592	H18			H19			H20			H21		
H15	O46	2.77041	H16	H33	2.95661	H17			H18			H19			H20			H21		
H15	O50	2.91170	H16	Ca7	2.98301	H17			H18			H19			H20			H21		
H22	O42	0.98588	H23	O42	0.98660	H24	O41	0.99754	H25	O48	0.98498	H26	O47	0.98243	H27	O47	0.99450	H28	O48	0.98088
H22	H23	1.58163	H23	H22	1.58163	H24	H21	1.59032	H25	H28	1.57886	H26	H27	1.58899	H27	H26	1.58899	H28	H25	1.57886
H22	O29	1.91449	H23	O32	1.87699	H24	O31	1.70417	H25	O18	1.89272	H26	O17	1.88627	H27	O20	1.73992	H28	O19	1.95113
H22	H6	2.15494	H23	H7	2.15003	H24	C11	2.43596	H25	H9	2.14808	H26	H10	2.12211	H27	C6	2.43921	H28	H12	2.07478
H22	O9	2.54313	H23	C12	2.50355	H24	H5	2.83299	H25	C8	2.53078	H26	C7	2.49549	H27	H10	2.65917	H28	C5	2.52406
H22	H7	2.69686	H23	H6	2.64503	H24	O35	2.93124	H25	H12	2.62744	H26	O7	2.69101	H27	O6	2.68011	H28	H9	2.64453
H22	O36	2.82367	H23	O36	2.79218	H24	H8	2.93412	H25	O8	2.73239	H26	Ca7	2.86542	H27	Ca7	2.83851	H28	O5	2.71256
			H23	O7	2.97205	H24			H25	O37	2.78268	H26	O38	2.88787	H27	H11	2.85030	H28	O37	2.74612
									H25	Ca8	2.87171	H26			H27	O38	2.98955	H28	Ca8	2.91374
H29	O45	0.99748	H30	O46	0.99081	H31	O46	0.98265	H32	O45	0.98460	H33	H29	1.58925	H34			H35		
H29	H32	1.58925	H30	H31	1.58606	H31	H30	1.58606	H32	H29	1.58925	H33	O23	1.85294	H34			H35		
H29	O22	1.72144	H30	O21	1.80278	H31	O24	1.92821	H32	O23	1.85294	H33	H16	2.16066	H34			H35		
H29	C2	2.42196	H30	H14	2.23119	H31	H15	2.12464	H32	H16	2.16066	H33	C3	2.49151	H34			H35		
H29	O2	2.65935	H30	C1	2.47815	H31	C4	2.55193	H32	C3	2.49151	H33	O3	2.71237	H34			H35		
H29	H16	2.69091	H30	H15	2.67389	H31	H14	2.70447	H32	O3	2.71237	H33	O39	2.81984	H34			H35		
H29	Ca5	2.83343	H30	O1	2.71669	H31	O4	2.74862	H32	O39	2.81984	H33	Ca5	2.85738	H34			H35		
H29	H13	2.85749	H30	O40	2.85346	H31	O40	2.82082	H32	Ca5	2.85738	H33			H34			H35		
H29	O39	2.87558	H30	Ca6	2.85690	H31	Ca6	2.88812	H32			H33			H34			H35		
			H30	O14	2.87981	H31			H32			H33			H34			H35		

475

H33	O49	0.97686	H34	O49	0.97560	H35	O50	0.98605	H36	O50	0.97905	H37	O51	0.97973	H38	O51	0.99205				
H33	H34	1.55468	H34	H33	1.55468	H35	H36	1.58568	H36	H35	1.58568	H37	H38	1.55005	H38	H37	1.55005				
H33	H10	2.34664	H34	O19	2.39218	H35	O49	1.84598	H36	O40	2.14165	H37	H8	2.04976	H38	O33	1.77829				
H33	H35	2.58196	H34	H12	2.50717	H35	H34	2.53067	H36	H11	2.17741	H37	O34	2.20072	H38	H4	1.97874				
H33	O38	2.66257	H34	H35	2.53067	H35	H13	2.56253	H36	H15	2.19988	H37	H2	2.24223	H38	H8	1.99179				
H33	O17	2.72932	H34	C5	2.65374	H35	H33	2.58196	H36	H13	2.35234	H37	H6	2.31981	H38	H1	2.35789				
H33	H14	2.94927	H34	C3	2.91240	H35	H11	2.60426	H36	H9	2.36458	H37	O36	2.45695	H38						
H33	H16	2.95661	H34	O3	2.96977				H36	O37	2.61085	H37	H3	2.66372							
H33	C7	2.98511							H36	H14	2.65940	H37	H7	2.81901							
									H36	O38	2.89925										
									H36	H12	2.99920										

$\text{Ca}_8\text{C}_{16}\text{O}_{32}(\text{H}_2\text{O})_{16}(\text{H}_2\text{O})_3$: structural water molecules are represented in blue, zeolitic molecules are represented in green.

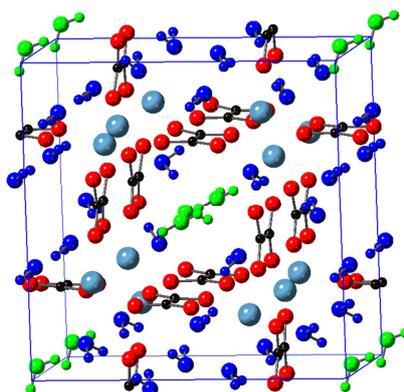



480

(c) selected O-H...O distances and number of H...O contacts with O-H...O $\leq 3\text{\AA}$ (highlighted in yellow) for COT. The atomic positions were optimized at the DFT level.

H1	O6	0.98194	H2	O6	1.01013	H3	O7	0.98972	H4	O5	1.00726	H5	O5	0.99237	H6	O7	0.98705
H1	H2	1.62553	H2	H1	1.62553	H3	H6	1.57438	H4	H5	1.61032	H5	H4	1.61032	H6	H3	1.57438
H1	O3	1.97834	H2	O1	1.66830	H3	O6	1.83746	H4	O2	1.67978	H5	O3	1.81868	H6	O5	1.95753
H1	H3	2.09660	H2	H3	2.15532	H3	H1	2.09660	H4	H6	2.08633	H5	H1	2.37604	H6	H4	2.08633
H1	H5	2.37604	H2	C1	2.61465	H3	H2	2.15532	H4	C1	2.60506	H5	C2	2.54822	H6	H5	2.66412
H1	C2	2.73894	H2	H4	2.75756	H3	H1	2.82312	H4	H2	2.75756	H5	H6	2.66412	H6	O2	2.80700
H1	H3	2.82312	H2	O4	2.79380	H3	O3	2.87563	H4	O7	2.83920	H5	O4	2.77186	H6	H4	2.84626
H1	O7	2.84845	H2	O4	2.96096	H3	O6	2.96615	H4	H6	2.84626	H5	O2	2.84989	H6	O2	2.85413
H1	O7	2.91450				H3	Ca1	2.98521	H4	O7	2.85001	H5	Ca1	2.91831			
H1	H4	2.93242							H4	H1	2.93242						
H1	O5	2.93253							H4	O1	2.99648						
H1	H1	2.95802															

485 **Data Availability.** All the data are shown in the figures of the paper. CIF files of COM, COD, COT structures: available upon request from the corresponding author.

Author Contributions. CL performed all syntheses and recorded most of the NMR spectra in strong collaboration with CB, DL and DI. CG and FT performed all DFT optimizations. FB and LB-C were deeply involved in the interpretation of the NMR spectra as well as MES and JVH. MD, EL and DB provided the KS sample and interpreted the data as physicians and a physical chemist, respectively. CB wrote the article in connection with his co-authors.

Competing Interests. The authors declare that they have no conflict of interest.

Acknowledgements. DFT calculations were performed using HPC resources from GENCI-IDRIS (Grant 097535). The UK 850 MHz solid-state NMR Facility used in this research was funded by EPSRC and BBSRC (contract reference PR140003), as well as the University of Warwick including via part funding through Birmingham Science City Advanced Materials Projects 1 and 2 supported by Advantage West Midlands (AWM) and the European Regional Development Fund (ERDF).

Financial Support. CL was funded by an Ecole Doctorale (ED 397) PhD fellowship of Sorbonne University.

References

- Bak, M., Thomsen, J.K., Jakobsen, H.J., Petersen, S.E., Petersen, T.E. and Nielsen, N.C.: Solid-state ^{13}C and ^{31}P NMR analysis of urinary stones, *J. Urol.*, 164, 856-863, doi: 10.1016/S0022-5347(05)67327-2, 2000.
- 500 Basso, R., Lucchetti, G., Zefiro, L. and Palenzona, A.: Caoxite, $\text{Ca}(\text{H}_2\text{O})_3(\text{C}_2\text{O}_4)$, a new mineral from the Cherchiarra mine, northern Apennines, Italy, *N. Jb. Miner. Mh.*, 2, 84-96, doi: 10.1127/njmm/1997/1997/84., 1997.
- Bazin, D., Letavernier, E., Haymann, J.-Ph., Frochot, V. and Daudon, M.: Crystalline pathologies in the human body: first steps of pathogenesis, *Ann. Biol. Clin.* 78, 4, 349-362, doi:10.1684/abc.2020.1557, 2020.
- 505



- Bazin, D., Haymann, J.-P. and Letavernier, E., Guest editors: From urolithiasis to pathological calcification: a journey at the interface between physics, chemistry and medicine. A tribute to Michel Daudon, C.R. Chimie, 19 (11-12), doi: 10.1016/j.crci.2016.10.001, 2016. All references therein are pertinent.
- 510
- Bazin, D., Daudon, M., Combes, C. and Rey, C.: Characterization and some physicochemical aspects of pathological microcalcifications, Chem. Reviews, 112, 5092-5120, doi: 10.1021/cr200068d, 2012.
- Bowers, G.M. and Kirkpatrick, R.J.: Natural abundance ^{43}Ca NMR as a tool for exploring calcium biomineralization: renal stone formation and growth, Cryst. Growth Des., 11, 5188-5191, doi: 10.1021/cg201227f, 2011.
- 515
- Butusov, M. and Jernelöv, A.: Phosphorus in the organic life: cells, tissues, organisms, 2013.
- Cavanagh, J., Fairbrother, W.J., Palmer III, A.G. and Skelton, N.J.: Protein NMR spectroscopy, second edition: principles and practice, Academic Press, 2007.
- 520
- Colas, H., Bonhomme-Coury, L., Diogo-Coelho, C., Tielens, F., Babonneau, F., Gervais, C., Bazin, D., Laurencin, D., Smith, M.E., Hanna, J.V., Daudon, M. and Bonhomme, C.: Whewellite, $\text{CaC}_2\text{O}_4\cdot\text{H}_2\text{O}$: structural study by a combined NMR, crystallography and modelling approach, CrystEngCom., 15, 43, 8840-8847, doi: 10.1039/C3CE41201F, 2013.
- 525
- Daudon, M., Bazin, D., André, G., Jungers, P., Cousson, A., Chevallier, P., Veron, E. and Matzen, G., Examination of whewellite kidney stones by scanning electron microscopy and powder neutron diffraction techniques, J. Appl. Crystallogr., 42, 109-115, doi : 10.1107/S0021889808041277, 2009.
- 530
- Dazem, C.L.F., Amombo Noa, F.M., Nenwa, J. and Öhtström, L.: Natural and synthetic metal oxalates – a topology approach, CrystEngComm, 21, 6156-6164, doi: 10.1039/c9ce01187k, 2019.
- Deganello, S.: The structure of whewellite, $\text{CaC}_2\text{O}_4\cdot\text{H}_2\text{O}$, at 328K, Acta Cryst., B37, 826-829, doi: 10.1107/S056774088100441X, 1981.
- 535
- Dessombz, A., Coulibaly, G., Kirakoya, B., Ouedraogo, R.W., Lengani, A., Rouzière, S., Weil, R., Picaut, L., Bonhomme, C., Babonneau, F., Bazin, D. and Daudon, M.: Structural elucidation of silica present in kidney stones coming from Burkina Faso, C.R. Chimie, 19, 1573-1579, doi: 10.1016/j.crci.2016.06.012, 2016.



- 540 Eckert, H., Yesinowski, J.P., Silver, L.A. and Stolper, E.M.: Water in silicate glasses: quantitation and structural studies by proton solid echo and magic angle spinning NMR methods, *J. Phys. Chem.*, 92, 2055-2064, doi: 10.1021/j100318a070, 1988.
- Feike, M., Demco, D.E., Graf, R., Gottwald, J., Hafner, S. and Spiess, H.W.: Broadband multiple-quantum NMR spectroscopy, *J. Magn. Reson. A*, 122, 214-221, doi: 10.1006/jmra.1996.0197, 1996.
- 545 Gan, Z., Hung, I., Wang, X., Paulino, J., Wu, G., Litvak, I.M., Gor'kov, P.L., Brey, W.W., Lendi, P., Schiano, J.L., Bird, M.D., Dixon, I.R., Toth, J., Boebinger, G.S. and Cross, T.A.: NMR spectroscopy up to 35.2T using a series-connected hybrid magnet, *J. Magn. Reson.*, 284, 125-136, doi: 10.1016/j.jmr.2017.08.007, 2017.
- 550 Gardner, L.J., Walling, S.A., Lawson, S.M., Sun, S., Bernal, S.A., Corkhill, C.L., Provis, J.L., Apperley, D.C., Iuga, D., Hanna, J.V. and Hyatt, N.C.: Characterization of and structural insight into struvite-K, $\text{MgKPO}_4 \cdot 6\text{H}_2\text{O}$, an analogue of struvite, *Inorg. Chem.*, 60, 195-205, doi: doi: 10.1021/acs.inorgchem.0c02802, 2021.
- 555 Gay, C., Letavernier, E., Verpont, M.-C., Walls, M., Bazin, D., Daudon, M., Nassif, N., Stéphan, O. and De Frutos, M.: Nanoscale analysis of Randall's plaques by electron energy loss spectromicroscopy: insight in early biomineral formation in human kidney: *ACS Nano*, 14, 1823-1836, doi: 10.1021/acsnano.9b07664, 2020.
- Gehl, A., Dietzsch, M., Mondeshki, M., Bach, S., Häger, T., Panthöfer, M., Barton, B., Kolb, U. and Tremel, W.: Anhydrous amorphous calcium oxalate nanoparticles from ionic liquids: stable crystallization intermediates in the formation of
560 whewellite, *Chem. Eur. J.*, 21, 18192-18201, doi: 10.1002/chem.201502229, 2015.
- Gervais, C., Laurencin, D., Wong, A., Pourpoint, F., Labram, J., Woodward, B., Howes, A.P., Pike, K.J., Dupree, R., Mauri, F., Bonhomme, C. and Smith, M.E.: New perspectives on calcium environments in inorganic materials containing calcium-oxygen
565 bonds: a combined computational-experimental Ca-43 NMR approach, *Chem. Phys. Lett.*, 464, 42-48, doi: 10.1016/j.cplett.2008.09.004, 2008.
- Godinot, C., Gaysinski, M. Thomas, O.P., Ferrier-Pagès, C. and Grover, R.: On the use of ^{31}P NMR for the quantification of hydrosoluble phosphorus-containing compounds in coral hosts tissues and cultures zooxanthellae, *Sci. Rep.*, 6, 21760, doi: 10.1038/srep21760, 2016.
- 570 Gopinath, T. and Veglia, G.: Probing membrane protein ground and conformationally excited states using dipolar- and J-coupling mediated MAS solid state NMR experiments, *Methods*, 148, 115-122, doi: 10.1016/j.ymeth.2018.07.003, 2018.



- 575 Heijnen, W., Jellinghaus, W. and Klee, W.E.: Calcium oxalate trihydrate in urinary calculi, *Urol. Res.*, 13, 281-283, doi: 10.1007/BF00262657, 1985.
- Huskic, I., Pekov, I.V., Krivovichev, S.V. and Friscic, T.: Minerals with metal-organic framework structures, *Sci. Adv.*, 2(8):e1600621, doi: 10.1126/sciadv.1600621, 2016.
- 580 Iuga, D., Schäfer, H., Verhagen, R. and Kentgens, A.P.M.: Populations and coherence transfer by double frequency sweeps in half-integer quadrupolar spin systems, *J. Magn. Reson.*, 147, 192-209, doi: 10.1006/jmre.2000.2192, 2000.
- Izatulina, A.R., Gurzhiy, V.V. and Franck-Kamenetskaya, O.V.: Weddellite from renal stones: structure refinement and dependence of crystal chemical features on H₂O content, *Am. Mineral.*, 99, 2-7, doi: 10.2138/am.2014.4536, 2014.
- 585 Jayalakshmi, K., Sonkar, K., Behari, A., Kapoor, V.K. and Sinha, N.: Solid state ¹³C NMR analysis of human gallstones from cancer and benign gall bladder diseases, *Solid State NMR*, 36, 60-65, doi: 10.1016/j.ssnmr.2009.06.001, 2009.
- Kresse, G. and Hafner, J., *Ab initio* molecular dynamics for liquid metals, *Phys. Rev. B*, 47, 558(R), doi: 590 10.1103/PhysRevB.47.558, 1993.
- Kresse, G. and Hafner, J., *Ab initio* molecular-dynamics simulation of the liquid-metal-amorphous-semiconductor transition in germanium, *Phys. Rev. B*, 49, 14251, doi: 10.1103/PhysRevB.49.14251, 1994.
- Kresse, G. and Furthmüller, J., Efficiency of *Ab-Initio* total energy calculations for metals and semiconductors using a 595 plane-wave basis set, *Comp. Mat. Sci.*, 6, 15-50, doi: 10.1016/0927-0256(96)00008-0, 1996.
- Leroy, C., Oxalates de calcium et hydroxyapatite : des matériaux synthétiques et naturels étudiés par des techniques RMN et DNP, Chapter 1, PhD thesis, Pierre et Marie Curie University, <http://www.theses.fr/19753385X>, 2016.
- 600 Lesage, A., Sakellariou, D., Hediger, S., Eléna, B., Charmont, P., Steuernagel, S and Emsley, L.: Experimental aspects of proton NMR spectroscopy in solids using phase-modulated homonuclear dipolar decoupling, *J. Magn. Reson.*, 163, 105-113, doi: 10.1016/s1090-7807(03)00104-6, 2003.
- 605 Li, Y., Reid, D.G., Bazin, D., Daudon M. and Duer, M.J.: Solid state NMR of salivary calculi: proline-rich salivary proteins, citrate, polysaccharides, lipids and organic-mineral interactions, *C.R. Chimie*, 19, 1665-1671, doi: 10.1016/j.crci.2015.07.001, 2016.



- Laurencin, D., Li, Y., Duer, M.J., Iuga, D., Gervais, C. and Bonhomme, C., A ^{43}Ca NMR perspective on octacalcium phosphate and its hybrid derivatives, *Magn. Reson. Chem.*, accepted, in the press, 2021.
- 610
- Laurencin, D. and Smith, M.E., Development of ^{43}Ca solid state NMR spectroscopy as a probe of local structure in inorganic and molecular materials, *Prog. Nucl. Magn. Reson. Spectr.*, 68, 1-40, doi: 10.1016/j.pnmrs.2012.05.001, 2013.
- Matlahov, I. and van der Wel, P.C.A.: Hidden motions and motion-induced invisibility: dynamics-based spectral editing in solid-state NMR, *Methods*, 148, 123-135, doi: 10.1016/j.ymeth.2018.04.015, 2018.
- 615
- Mroue, K.H., Xu, J., Zhu, P., Morris, M.D. and Ramamoorthy, A.: Selective detection and complete identification of triglycerides in cortical bone by high-resolution ^1H MAS NMR spectroscopy, *Phys. Chem. Chem. Phys.*, 18, 18687-18691, doi: 10.1039/C6CP03506J, 2016.
- 620
- Paruzzo, F.M. and Emsley, L.: High-resolution ^1H NMR of powdered solids by homonuclear decoupling, *J. Magn. Reson.*, 309, 106598, doi: 10.1016/j.jmr.2019.106598, 2019. A recent review of CRAMPS methods at moderate MAS with advantages and drawbacks.
- 625
- Petit, Y., Belletti, G.D., Debroise, T., Llansola-Portoles, M.J., Lucas, I.T., Leroy, C., Bonhomme, C., Bonhomme-Coury, L., Bazin, D., Letavernier, E., Haymann, J.-P., Frochot, V., Babonneau, F., Quaino, P. and Tielens, F., Vibrational signatures of calcium oxalate polyhydrates, *Chemistry Select*, 3, 8801-8812, doi: 10.1002/slct.201801611, 2018.
- Pourpoint, F., Gervais, C., Bonhomme-Coury, L., Azaïs, T., Coelho, C., Mauri, F., Alonso, B., Babonneau, F. and Bonhomme, C.: Calcium phosphates and hydroxyapatite: solid-state NMR experiments and first-principles calculations, *Appl. Magn. Reson.*, 32, 435-457, doi: 10.1007/s00723-007-0040-1, 2007.
- 630
- Reid, D.G., Jackson, G.J., Duer, M.J. and Rodgers, A.L.: Apatite in kidney stones is a molecular composite with glycosaminoglycans and proteins; evidence from Nuclear Magnetic Resonance spectroscopy, and relevance to Randall's plaque pathogenesis and prophylaxis, *J. Urol.*, 185, 725-730, doi: 10.1016/j.juro.2010.09.075, 2011.
- 635
- Reid, D.G., Duer, M.J., Jackson, G.E., Murray, R.C., Rodgers, A.L. and Shanahan, C.M.: Citrate occurs widely in healthy and pathological apatitic biomineral: mineralized articular cartilage and intimal atherosclerotic plaque and apatitic kidney stones, *Calcif. Tissue Inter.*, 93, 253-260, doi: 10.1007/s00223-013-9751-5, 2013.
- 640



- Ren, J., Dimitrov, I., Sherry, A. and Malloy, C.: Composition of adipose tissue and marrow fat by ^1H MR spectroscopy at 7 Tesla, *J. Lipid Res.*, 49, 2055-2062, doi: 10.1194/jlr.D800010-JLR200, 2008.
- 645 Ruiz-Agudo, E. Burgos-Cara, A., Ruiz-Agudo, C., Ibanez-Velasco, A., Cölfen, H. and Rodriguez-Navarro, C.: A non-classical view on calcium oxalate precipitation and the role of citrate, *Nature Commun.*, 8:768, doi: 10.1038/s41467-017-00756-5, 2017.
- Samoson, A., see: <https://goneamericas.com/mas-probes-magic-angle-spinning/>, 2019.
- Schmidt-Rohr, K. and Spiess, H.W.: *Multidimensional solid-state NMR and polymers*, Acad. Press. Elsevier, 1994.
- 650 Shepelenko, M., Feldman, Y., Leiserowitz, L. and Kronik, L.: Order and disorder in calcium oxalate monohydrate: insights from first-principles calculations, *Cryst. Growth Des.*, 20, 858-865, doi: 10.1021/acs.cgd.9b01245, 2019.
- 655 Sherer, B.A., Chen, L., Kang, M., Shimotake, A.R., Wiener, S.V., Chi, T., Stoller, M.L. and Ho, S.P.: A continuum of mineralization from human renal pyramid to stones on stems, *Acta Biomater.*, 71, 72-85, doi: 10.1016/j.actbio.2018.01.040, 2018.
- Smith, M.E.: Recent progress in solid-state nuclear magnetic resonance of half-integer spin low- γ quadrupolar nuclei applied to inorganic materials, *Magn. Reson. Chem.*, 1-44, doi: 10.1002/mrc.5116, 2020. And reference therein.
- 660 Steiner, T.: The hydrogen bond in the solid state, *Angew. Chemie*, 41, 48-76, doi:10.1002/1521-3773(20020104)41:1<48::AID-ANIE48>3.0.CO;2-U, 2002.
- 665 Tazzoli, V. and Domeneghetti, C.: The crystal structure of whewellite and weddellite: re-examination and comparison, *Am. Mineral.*, 65, 327-334, 1980.
- Tielens, F., Vekeman, J., Bazin, D. and Daudon, M., C.R. Chimie, accepted for publication, 2021.
- 670 Wong, A., Howes, A.P., Dupree, R. and Smith, M.E.: Natural abundance Ca-43 study of calcium-containing organic solids: a model study for Ca-binding biomaterials, *Chem. Phys. Lett.*, 427, 201-205, doi: 10.1016/j.cplett.2006.06.039, 2006.