Solid-state ¹³C-NMR spectroscopic determination of sidechain mobilities in zirconium-based metal-organic frameworks

Günter Hempel¹, Ricardo Kurz¹, Silvia Paasch², Kay Saalwächter¹, and Eike Brunner²

Correspondence: Günter Hempel (guenter.hempel@physik.uni-halle.de)

Abstract. Porous Interpenetrated Zirconium-Organic Frameworks (PIZOFs) are a class of Zr-based metal-organic frameworks (MOFs) which are composed of long, rodlike dicarboxylate linkers and Zr₆O₄(OH)₄(O₂C)₁₂ nodes. Long oligoethylene glycol or aliphatic side chains are covalently attached to the linker molecules in the case of PIZOF-10 and PIZOF-11, respectively. These side chains are supposedly highly mobile thus mimicking a solvent environment. It is anticipated that such MOFs could be used as solid catalyst - the MOF - with pore systems showing properties similar like a liquid reaction medium. To quantify the side chain mobility, we have here applied different 1D and 2D NMR solid-state spectroscopic techniques like cross polarization (CP) and dipolar-coupling chemical-shift correlation (DIPSHIFT) studies. The rather high ¹H-¹³C CP efficiency observed for the CH₂ groups of the side chains indicates that the long side chains are unexpectedly immobile or at least that their motions are strongly anisotropic. More detailed information about the mobility of the side chains was then obtained from DIPSHIFT experiments. Analytical expressions for elaborate data analysis are derived. These expressions are used to correlate order parameters and slow motional rates with signals in indirect spectral dimension thus enabling the quantification of order parameters for the CH₂ groups. The ends of the chains are rather mobile whereas the carbon atoms close to the linker are stronger spatiallly restricted in mobility.

1 Introduction

Metal-organic frameworks (MOFs) are crystalline porous materials (Kitagawa et al., 2004; Ferey, 2008; Tranchemontagne et al., 2009; Kaskel, 2016) composed of organic and inorganic building units forming networks with micro- and/or mesopores. Due to promising properties such as an extraordinarily high specific surface area and gas storage capacity, MOFs are assumed to find numerous applications, e.g., in gas storage and separation, drug delivery, sensing, and wastewater treatment (Horcajada et al., 2006; Ke et al., 2011; Maurin et al., 2017; Li et al., 2019; Lawson et al., 2021; Maranescu and Visa, 2022; Liu et al., 2023). Favorable MOFs for catalysis (Pascanu et al., 2019; Remya and Kurian, 2019; Bavykina et al., 2020; Gao et al., 2022) should be stable at elevated temperatures and in the presence of moisture. Most members of the PIZOF (Porous Interpenetrated Zirconium-Organic Framework) family (Schaate et al., 2011; Roy et al., 2012; Lippke et al., 2017) are very stable and insensitive to moisture in contrast to other MOFs containing, e.g., Zn instead of Zr (Kaye et al., 2007; Feng et al., 2010) which makes this type of MOFs particularly interesting for catalytic applications. PIZOFs contain long dicarboxylates as linkers (cf. Fig. 1)

¹Martin-Luther-Universität Halle-Wittenberg, Institut für Physik – NMR, Betty-Heimann-Str. 7, 06120 Halle, Germany

²Technische Universität Dresden, Fakultät für Chemie und Lebensmittelchemie, Bioanalytische Chemie, 01062 Dresden, Germany

Figure 1. Structural formulae of the linkers for the herein studied PIZOF's: PIZOF-2, PIZOF-10, and PIZOF-11.

30

and Zr₆O₄(OH)₄(O₂C)₁₂ as nodes. The surface properties of the internal pore system including its polarity can be tuned in PIZOFs by adding appropriate side chains to the linkers. Examples are PIZOF-10 and PIZOF-11 (see Fig. 1). Both exhibit high thermal stability and resistance against atmospheric moisture like other members of the PIZOF family (Lippke et al., 2017). The aliphatic side chains make the internal surface of PIZOF-11 hydrophobic whereas PIZOF-10 with its oligoethylene glycol side chains is rather hydrophilic.

The long oligoethylene glycol or aliphatic side chains in PIZOF-10 and PIZOF-11 are supposed to be highly flexible thus providing a liquid-like environment in the remaining pores. In order to test this hypothesis, solid-state NMR techniques were applied to evaluate the side chain mobility. Solid-state NMR spectroscopy is a powerful tool for determining structural parameters and detecting mobile structural elements in biological systems as well as various materials (Renault et al., 2010; Paasch and Brunner, 2010; Duer, 2002). The framework structure of MOFs can be studied in general by ¹H, ¹³C or ¹⁷O magic angle spinning (MAS) NMR spectroscopy (Loiseau et al., 2005; Klein et al., 2012; Lucier et al., 2018; Bignami et al., 2018; Brunner and Rauche, 2020). Furthermore, nuclei such as ²⁷Al (Jiang et al., 2010; Lieder et al., 2010; Petrov et al., 2020), ⁷¹Ga (Volkringer et al., 2007; Hajjar et al., 2011), ⁴⁵Sc (Mowat et al., 2011), and others (He et al., 2014) can be used in order

to detect the environment of the central metal atom. NMR spectroscopy also allows the study of host/guest interactions with adsorbed species (Wong et al., 2019; Witherspoon et al., 2018; Yan et al., 2017; Wittmann et al., 2019).

It is well-known that the efficiency of the cross polarization (CP) experiment (Pines et al., 1973) is strongly influenced by the presence of thermal motions (Schulze et al., 1990). This has been exploited previously in order to qualitatively characterize the mobility of aliphatic chains, e.g. of n-alkylsilanes bonded to silica surfaces (Sindorf and Maciel, 1983), of surfactants in mesoporous MCM-41 materials (Simonutti et al., 2001), and alkanes grafted to silica for chromatography (Pursch et al., 1996).

The motion of the side chains is expected to be anisotropic because of its fixation at the middle ring of the linker backbone. The degree of anisotropy (expressed e.g. by the order parameter S) resolved for individual atomic positions might be an important characteristic of the chain motion. More detailed information can be obtained by some 2D NMR methods. In the work presented here, the DIPSHIFT (dipolar-coupling chemical-shift correlation) technique was applied in order to site-specifically determine order parameters. A pulse scheme of this sequence is shown in the SI. It was developed as separated-local-field experimment under MAS (Munowitz et al., 1981; Schaefer et al., 1983). Applications made use of the possibility to determine the residual dipolar coupling site-specifically (de Azevedo et al., 2008; Bärenwald et al., 2016) and a recent paper compares the results with those of rotational echo double resonance (REDOR, Jain et al. (2019)). The DIPSHIFT experiment enables correlation of isotropic chemical shifts, i.e. atomic positions, in direct dimension (t_2) with signals in the indirect dimension (t_1) corresponding to an FID which solely evolves under MAS-modulated $^1H - ^{13}C$ dipolar couplings between subsequent rotational echoes. The latter is true under the condition that protons coupled to the considered nucleus do not undergo interactions with each other and provided that Fourier transform is performed in direct dimension only. The depth of the minimum between consecutive echoes is a measure for the (residual) dipolar coupling which itself contains information about the order parameter. The decrease of the 2nd echo with respect to the first one represents the influence of intermediate motions (intermediate-motional T_2 effect).

To determine the mobility site-selectively, ¹³C signal assignment was necessary. This was achieved by the application of techniques such as solid-state attached proton test (APT, Lesage et al. (1998b); Hoffmann et al. (2012)), ¹H-¹³C heteronuclear correlation (HETCOR), and ¹H-¹³C heteronuclear multiple-quantum coherence (HMQC, Lesage et al. (1998a)).

The analysis of DIPSHIFT data was in the past usually performed by comparison with numerically calculated data under parameter variation. In this paper, analytical expressions were derived and used. This allowed to estimate the parameter set for best data fitting in a more efficient way. Intermediate motions were included in the analytical expressions by application of the Anderson-Weiss procedure (Anderson and Weiss, 1953). Specifically, we focus on the conditions under which the signal damping arising from intermediate motions can be described by an exponential function. The theoretical background of this procedure is described in the next section.

2 Equations / models for DIPSHIFT data evaluation

2.1 Derivation

85

90

MAS experiments on samples with anisotropic spin interactions result in spectra with spinning sidebands (SSB) and in FID's containing echo trains. Provided that the anisotropic interaction is described by a second-order tensor, the SSB intensities can be efficiently calculated by polynomial expressions following Hempel et al. (2021). Eqn. (21) in that paper gives the general equation for the intensity $S_m(D/\omega_r, \eta)$ of the m-th order sideband; the parameters in the argument list are the anisotropy D of the tensor, the angular spinning frequency ω_r , and the asymmetry parameter η of the tensor. A closed-form evaluation of this equation is hardly possible; equations for SSB which are ready for use must be obtained by symbolic-language software. Examples for low-order SSB are given in the mentioned paper.

The FID can be calculated as Fourier synthesis if the SSB intensities are known:

$$F(t) = \sum_{m = -\infty}^{\infty} S_m \left(\frac{D}{\omega_{\rm r}}, \eta\right) e^{im\omega_{\rm r}t} \tag{1}$$

Applying this formalism to spin systems where chemical-shift anisotropy is the dominating interaction is straightforward. In the case of dipolar interaction, however, some special aspects have to be considered:

- Fast anisotropic thermal motion: The tensor is subjected to a partial averaging process over all possible states which occur during this motion. Then anisotropy and asymmetry parameter of this averaged tensor have to be inserted into the SSB polynomials. In this paper, this case has to be considered for modelling two-site jumps.
- Dipolar interaction with more than one spin: Tensors of the individual couplings have to be added up. If, however, the neighbouring spins interact among themselves, it is possible that the total interaction is represented by a tensor of order
 2. In the latter case the polynomial formulae mentioned above would not be applicable.
 - In the case of multispin interactions, different combinations of spin orientations have to be taken into account; they can lead to different effective tensors. Each of these tensors corresponds to a particular set of SSB $\{S_m^k\}$ where k indicates the respective combination of spin orientations. The SSB intensity which appears in the experiment is the average of the SSB intensities belonging to all combinations: $S_m = \sum_k S_m^k$. This procedure is applied below for the calculation of FID's of both CH₂ and CH₃ groups.

2.2 Transformation to a cosine series

In this paper we consider dipolar interactions between spins 1/2. The observed spin can be oriented parallel or antiparallel to \mathbf{B}_0 with approximately equal probabilities at not too low temperatures. A change of orientation of the observed spin inverts the anisotropy of the dipolar tensor assuming the configuration of the coupled spins remains unchanged. We thus always have pairs of tensors with inverted anisotropy (D and (-D)) but equal asymmetry parameter. Applying the relation (see Hempel

et al. (2021))

$$S_m\left(\frac{D}{\omega_{\rm r}},\eta\right) = S_{-m}\left(-\frac{D}{\omega_{\rm r}},\eta\right) \tag{2}$$

the exponential series of eqn. (1) can be transformed always into a cosine series:

$$100 \quad F(t) = \sum_{m=0}^{\infty} C_m \cos m\omega_{\rm r} t \tag{3}$$

with the following definitions:

$$C_0 := S_0; \quad C_m \left(\frac{D}{\omega_r}, \eta \right) := S_m \left(\frac{D}{\omega_r}, \eta \right) + S_{-m} \left(\frac{D}{\omega_r}, \eta \right) = S_m \left(\frac{D}{\omega_r}, \eta \right) + S_m \left(-\frac{D}{\omega_r}, \eta \right)$$

$$\tag{4}$$

Therefore, the C_m contain only even powers of D/ω_r .

In the following, the polynomial equations are established for four situations which may occur in the PIZOF samples.

105 2.3 Model 1: Ensemble of isolated spin pairs

The coefficients are denoted by $C_m^{\rm IS}$ and can be taken immediately from the generic equation by using the dipolar coupling constant D_0 as anisotropy and zero asymmetry parameter. As an example, up to 12th order we have:

$$C_0^{\text{IS}} = 1 - \frac{3}{20} \left(\frac{D_0}{\omega_r}\right)^2 + \frac{227}{181440} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{1103}{2306304} \left(\frac{D_0}{\omega_r}\right)^6 + \frac{22859}{1792327680} \left(\frac{D_0}{\omega_r}\right)^8 - \frac{3308407}{14302774886400} \left(\frac{D_0}{\omega_r}\right)^{10} + \frac{108665671}{35886962442240000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(5)$$

The polynomial equations for m = 1 to 3 are given in section 7.

110 2.4 Model 2: Spin pairs with fast 2-site jumps

115

"Fast" means that the motional average is already complete at times which are relevant for the experiment. For DIPSHIFT experiments, this is the times between the end of excitation and the beginning of data acquisition. Thus, the averaging must already be complete at the first time step in the indirect dimension which is one order of magnitude smaller than the rotation period, i.e. about 20 μ s. In the case of cross-polarization, this relevant time is of the order of the reciprocal of the dipolar coupling constant, i.e. also about 10^{-5} s. The coefficients for model 2 are denoted by $C_m^{\text{IS-j}}$. The characteristical tensor is the average $\langle \mathbf{D} \rangle$ of the tensors of both sites \mathbf{D}_1 and \mathbf{D}_2 , see Fig. 2. We suppose that the sites are occupied with equal probability. The angle between the dipolar axes of both sites is 2α . In a frame where the z axis is along the bisector, the y axis is perpendicular to the plane spanned by the IS connection vectors of both sites, and the x axis is in this plane perpendicular to the bisector, both tensors are represented by the matrices D_1 and D_2 as

120
$$D_{1;2} = D_0 \begin{pmatrix} \frac{1}{2} - P_2(\cos \alpha) & 0 & \pm \frac{3}{4}\sin 2\alpha \\ 0 & -\frac{1}{2} & 0 \\ \pm \frac{3}{4}\sin 2\alpha & 0 & P_2(\cos \alpha) \end{pmatrix}$$
 (6)

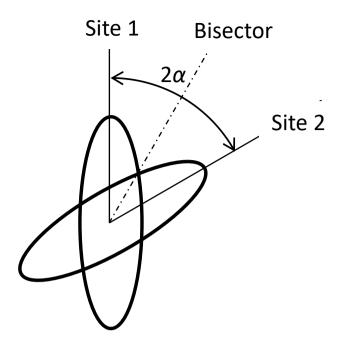


Figure 2. Two-site jumps between positions differing by an angle of 2α .

The average of both matrices is diagonal in this bisector frame:

$$\langle D \rangle = D_0 \begin{pmatrix} \frac{1}{2} - P_2(\cos \alpha) & 0 & 0\\ 0 & -\frac{1}{2} & 0\\ 0 & 0 & P_2(\cos \alpha) \end{pmatrix}$$
(7)

Particularly, in this work, 180° ring flips are of interest. That means the flip angle for the CH bonds is $2\alpha = 120^{\circ}$:

$$\langle D \rangle_{120}^{\circ} = D_0 \begin{pmatrix} \frac{5}{8} & 0 & 0 \\ 0 & -\frac{1}{2} & 0 \\ 0 & 0 & -\frac{1}{8} \end{pmatrix}$$
 (8)

In the latter case, the anisotropy is $\frac{5}{8}D_0$ and the magnitude of the asymmetry parameter is $\eta = \frac{3}{5}$. The cos Fourier coefficients are

$$C_m^{\text{IS-j}} = C_m \left(\frac{5D_0}{8\omega_{\text{r}}} \,,\, \frac{3}{5} \right) \tag{9}$$

The explicit polynomial equations can be found in section 7.

2.5 Model 3: IS₂ spin system

Here it is assumed that the observed spin I interacts with two neighbouring spins S. The coupling constant for each single coupling is equal to D_0 , i.e. the distances between I and both S are assumed to be equal. There are four combinations of

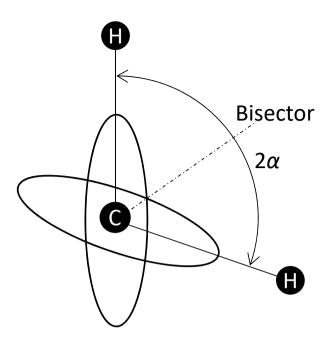


Figure 3. ¹H positions within a CH₂ group. The angle between the C-H connection vectors is 2α . Supposing tetrahedral symmetry, $\alpha = \arccos(1/\sqrt{3})$.

the S spin orientations. The two combinations where the two S_z are parallel generate the tensor \mathbf{D}_{Σ} and the two ones with antiparallel S_z generate the tensor \mathbf{D}_{Δ} . In the bisector frame (see Fig. 3), the tensor matrices are the same as in eqn. (6). The matrices of sum and difference tensor for tetrahedral symmetry are

135
$$D_{\Sigma} = D_0 \begin{pmatrix} 1 & 0 & 0 \\ 0 & -1 & 0 \\ 0 & 0 & 0 \end{pmatrix}, \qquad D_{\Delta} = D_0 \begin{pmatrix} 0 & 0 & \sqrt{2} \\ 0 & 0 & 0 \\ \sqrt{2} & 0 & 0 \end{pmatrix},$$
 (10)

respectively. From D_{Σ} we can read off directly the anisotropy as D_0 and the asymmetry parameter $\eta=1$. D_{Δ} has an eigenvalue vector $(0, D_0\sqrt{2}, -D_0\sqrt{2})$ which gives anisotropy $D_0\sqrt{2}$ and $\eta=1$. Hence the cosine coefficients for a tetrahedral IS₂ spin system are

$$C_m^{\text{IS2}} = \frac{1}{2} \left[C_m \left(\frac{D_0}{\omega_{\text{r}}} , 1 \right) + C_m \left(\frac{D_0 \sqrt{2}}{\omega_{\text{r}}} , 1 \right) \right] \tag{11}$$

140 The polynomial equations can again be found in section 7.

2.6 Model 4: Rapidly rotating methyl groups

Here we consider the special case of an IS_3 spin system: The observed spin I resides in the middle of a tetrahedron, the three IS bonds have equal length and point into three corners of this tetrahedron, and the rotation axis points into the remaining corner,

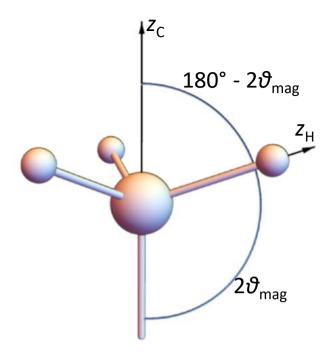


Figure 4. Geometry of a CH₃ group.

see Fig. 4. The tensor of a single CH coupling in a frame, the z axis of which is along the rotation axis, has the matrix

145
$$D_1 = D_0 \begin{pmatrix} \frac{1}{6} + \frac{2}{3}\cos 2\varphi & \frac{2}{3}\sin 2\varphi & \frac{\sqrt{2}}{3}\cos\varphi \\ \frac{2}{3}\sin 2\varphi & \frac{1}{6} - \frac{2}{3}\cos 2\varphi & \frac{2}{3}\sin 2\varphi \\ \frac{\sqrt{2}}{3}\cos\varphi & \frac{2}{3}\sin 2\varphi & -\frac{1}{3} \end{pmatrix}$$
; (12)

where φ is the instantaneous rotation angle around the z axis. Averaging over this angle, which is equivalent to fast-limit time averaging corresponding to a methyl group at not too low temperatures, gives for all three couplings a tensor matrix which is diagonal in this frame:

$$\langle D \rangle_{\varphi} = D_0 \begin{pmatrix} 1/6 & 0 & 0 \\ 0 & 1/6 & 0 \\ 0 & 0 & -1/3 \end{pmatrix} \tag{13}$$

150 There are 8 spin orientation permutations of the three S spins, see table 1:

Regarding that the anisotropy enters the C_m equations in even powers only, the cosine coefficients are

$$C_m^{\text{CH3}} = \frac{1}{4} C_m \left(\frac{D_0}{\omega_r} , 0 \right) + \frac{3}{4} C_m \left(\frac{D_0}{3\omega_r} , 0 \right)$$
 (14)

The explicit polynomial equations can again be found in section 7.

Spins	Total tensor	sum matrix	anisotropy	η
$\uparrow \uparrow \uparrow \uparrow$	$\mathbf{D}_1 + \mathbf{D}_2 + \mathbf{D}_3$	$3\langle D\rangle_{\varphi}$	$-D_0$	0
$\downarrow \uparrow \uparrow \uparrow$	$-\mathbf{D}_1+\mathbf{D}_2+\mathbf{D}_3$	$\langle D \rangle_{arphi}$	$-D_0/3$	0
$\uparrow\downarrow\uparrow$	${f D}_1 - {f D}_2 + {f D}_3$	$\langle D \rangle_{arphi}$	$-D_0/3$	0
$\uparrow \uparrow \downarrow$	${f D}_1 + {f D}_2 - {f D}_3$	$\langle D \rangle_{arphi}$	$-D_0/3$	0
$\uparrow \downarrow \downarrow$	${f D}_1 - {f D}_2 - {f D}_3$	$-\langle D \rangle_{\varphi}$	$D_0/3$	0
$\downarrow\uparrow\downarrow$	$-\mathbf{D}_1+\mathbf{D}_2-\mathbf{D}_3$	$-\langle D \rangle_{\varphi}$	$D_0/3$	0
$\downarrow\downarrow\uparrow\uparrow$	$-\mathbf{D}_1 - \mathbf{D}_2 + \mathbf{D}_3$	$-\langle D \rangle_{\varphi}$	$D_0/3$	0
$\downarrow\downarrow\downarrow$		$-3\langle D\rangle_{\varphi}$	D_0	0

Table 1. All possibilities to combine the orientations of the three proton spins in a CH₃ group. Anisotropy and matrix of the sum tensor are displayed in the neighboured columns.

2.7 Influence of remote protons

Because of the r^{-3} dependence of the dipolar coupling, the dipolar environment of protonated carbons is essentially determined by the directly bound proton(s) located at a distance of about 1.1 Å. The situation is less unique for nonprotonated carbons, where often several remote protons with similar distances to the regarded carbon are relevant. Then, many details of the molecular geometry have to be considered to establish a model function. On the other hand, a restriction to allegedly dominant protons can be a reason for incorrect data analysis. As an attempt, the cosine coefficients C_m were calculated for the acetylenic carbons considering the closest protons of each neighboring ring. Comparing this model function with experimental data, however, showed that the former does not reflect the real situation; the residual couplings obtained by the analysis are still larger that the full coupling expected from the model. Consequently we restricted the DIPSHIFT evaluations to protonated carbons.

2.8 Fast anisotropic motion

- As mentioned above, fast-limit averaging means that motional averaging is complete at times which are relevant for the experiment. The effect of fast-motional averaging can be described by tensor matrices with elements changed compared to the rigid case, hence also anisotropy and asymmetry parameter change. Two general cases can be distinguished:
 - All three eigenvalues are decreased by a common factor which is called order parameter S. Then also the anisotropy is reduced by the same factor; the asymmetry parameter stays constant. The variable D_0 in the functions from above is then replaced by the residual dipolar coupling $D_{\text{res}} = S \cdot D_0$. Relevant examples are uniaxial rotation or rotational jumps between 3 or more equally distributed and populated sites.
 - The tensor eigenvalues change during the averaging process in different manner. Then the introduction of a single order parameter will not provide an adequate description of the situation, anisotropy and asymmetry parameter change non-trivially and a new function has to be used. As an example, consider the above case of 2-site jumps: The function $C_m^{\rm IS}$

had to be replaced by $C_m^{\text{IS-j}}$. This means that the asymmetry is reduced, but at the same time the asymmetry parameter increases from 0 (case of C_m^{IS}) to 3/5 (case of $C_m^{\text{IS-j}}$). Thus, the tensor principal values of one case can no longer be represented as common multiples of the principal values of the other.

2.9 Intermediate motions

175

Intermediate motions, i.e. motions with a rate in the range of the static-limit dipolar coupling constant and/or the spinning frequency, interfere with the refocusing effect of MAS. This manifests itself by a damping of the rotational echoes or even by their complete disappearance. A rather weak echo damping is observed in our data sets. To analyze these we need an analytical expression for this case, for which we took a heuristic approach of multiplying of the rigid-lattice model functions derived above by an exponential damping function. The relevant questions are under which conditions this can be an appropriate approximation and whether the fitted decay constant contains information on the motional timescale.

An approximate analytical expression for the MAS FID $F_{AW}(t)$ during slow or intermediate motion was derived by Hirschinger (2006) using the Anderson-Weiss (AW) formalism (Anderson and Weiss, 1953):

$$F_{\text{AW}}(t) = \exp\left\{-\int_{0}^{t} (t - \tau) K(\tau) d\tau\right\}$$
(15)

 $K(\tau)$ is the orientation autocorrelation function of the motion under consideration. In the case of MAS, the expression derived by Clough and Gray (1962)

190
$$K(\tau) = e^{-\tau/\tau_c} \left(\frac{2}{3} \cos \omega_r \tau + \frac{1}{3} \sin \omega_r \tau \right)$$
, (16)

containing an assumed exponential decay describing the random motion with correlation time τ_c , multiplied by the coherent (oscillatory) correlation function of the MAS rotation, was inserted into eqn. (15). This gave

$$F_{AW}(t) = \exp\left\{-\frac{1}{3}M_{2}t\left(\frac{2\tau_{c}}{1+(\omega_{r}\tau_{c})^{2}} + \frac{\tau_{c}}{1+4(\omega_{r}\tau_{c})^{2}}\right) + \frac{1}{3}M_{2}\tau_{c}^{2}\left[2\frac{1-(\omega_{r}\tau_{c})^{2}}{\left(1+(\omega_{r}\tau_{c})^{2}\right)^{2}}\left(1-e^{-t/\tau_{c}}\cos\omega_{r}t\right) + \frac{1-4(\omega_{r}\tau_{c})^{2}}{\left(1+4(\omega_{r}\tau_{c})^{2}\right)^{2}}\left(1-e^{-t/\tau_{c}}\cos2\omega_{r}t\right)\right] + \frac{4}{3}M_{2}\tau_{c}^{2}e^{-t/\tau_{c}}\left[\frac{\sin\omega_{r}t}{\left(1+(\omega_{r}\tau_{c})^{2}\right)^{2}} + \frac{\sin2\omega_{r}t}{\left(1+4(\omega_{r}\tau_{c})^{2}\right)^{2}}\right]\right\}$$

$$(17)$$

This equation describes a dipolar FID, which is an echo train for large τ_c or a monotoneous decay for fast motion, i.e. short τ_c .

The echo-train structure is widely lost already in the vicinity of $\omega_r \tau_c = 1$. However, it is an approximate expression because the AW approach restricts the cumulant expansion of the distribution of the reduced phase $\varphi := (1/t) \int_0^t \omega(t_1) dt_1$ to the second-order term. Hence, all reduced-phase distributions are regarded as Gaussian distributions within the AW treatment because only for Gaussian distributions all cumulants with order > 2 disappear. This could be a good approximation for short times

 $(t \ll M_2^{-1/2})$ (de Azevedo et al., 2008) as well as for long times $(t \gg \tau_c)$. The reason for this is (i) that for short times, higher cumulants (order 2n) are still without influence because they are connected with $t^{2n}/(2n)!$; (ii) for long times, the reduced-phase distribution changes gradually toward a Gaussian distribution. The latter can be rationalized by means of the central limiting theorem, which states that the cumulants of order >2 decrease if a stochastic variable (here: reduced phase) is the sum or integral of another stochastic variable (here: frequency).

In between we expect a "gap of validity". Obviously, for sufficiently short correlation times ($\tau_{\rm c} \ll M_2^{-1/2}$) there is an overlap of both regions; here a gap of validity does not appear. For a rigid lattice, however, this gap ranges formally until infinity. For DIPSHIFT applications we have to consider that the data are usually plotted versus $t_1/T_{\rm r} = \omega_{\rm r} t_1/(2\pi)$ in the interval [0,1]. To ensure that this interval does not reach essentially into the validity gap, $\max t_1 = T_{\rm r}$ should be smaller than $\sqrt{5}/D_0$, in other words $D_0/\omega_{\rm r} < \approx 0.36$. In fact, a numerical comparison of model function 1 (equation (5)) with equation (17) for $\tau_{\rm c} \to \infty$ and $M_2 \to D_0^2/5$ shows that deviations become relevant if this threshold is exceeded.

de Azevedo et al. (2008) investigated the quality of the AW approximation for the DIPSHIFT experiment by comparison of eqn. (17) with numerically calculated data. Their results show that the deviations between eqn. (17) and experimental data are maximum in the intermediate region. Cobo et al. (2014) did that in a similar manner for a related (recoupled) experiment, rec-DIPSHIFT. This concerns situations where the echo structure of the FID is damped strongly.

Conversely, if we observe a weak damping of the echo train we may conclude that the influence of intermediate motions is negligible (except fast motions, see above). This means that in this case, $\omega_r \tau_c \gg 1$. With this condition, eqn. (17) can be simplified to

$$F_{\rm AW}(t) \approx F_{\rm rigid}(t) \cdot \exp\left\{-\frac{t}{T_{\rm 2MAS}}\right\} = F_{\rm rigid}(t) \cdot \exp\left\{-\frac{1}{f_{\rm r}T_{\rm 2MAS}} \cdot \frac{t}{T_{\rm r}}\right\} , \tag{18}$$

where $F_{\text{rigid}}(t)$ denotes the FID without slow thermal motion and f_{r} is the spinning frequency of the sample; the damping constant is defined as

$$220 \quad \frac{1}{T_{2\text{MAS}}} := \frac{3}{4} \frac{M_2}{\omega_{\rm r}^2 \tau_{\rm c}} \ . \tag{19}$$

It is notable that the damping constant is proportional to $f_{\rm r}^{-2}$ in a plot vs. t and even proportional to $f_{\rm r}^{-3}$ in the DIPSHIFT-typical plot vs. $t/T_{\rm r}$. Numerical studies showed that the condition $\tau_{\rm c} \ll T_{\rm r}$ is tied to the intensity of the first rotational echo being at least half of the initial value.

The static part of eqn. (17) is obtained for $\tau_c \to \infty$ as

225
$$F_{\text{rigid,AW}} = \exp\left\{-\frac{M_2}{3\omega_{\text{r}}^2} \left[2(1-\cos\omega_{\text{r}}t) + \frac{1}{4}(1-\cos2\omega_{\text{r}}t)\right]\right\}$$
 (20)

We have confirmed numerically that relevant deviations from the polynomial formulae occur if D_0/ω_r is comparable to or larger than 0.5. Consequently, $F_{\text{rigid}}(t)$ in eqn. (18) is represented by eqn. (3), where the C_m are the corresponding coefficients derived for the four models shown above.

2.10 Second moment

230 The equations derived by the AW approach contain the second moment M_2 of the overall dipolar interactions:

$$M_2 \equiv \langle \omega^2 \rangle = \int \omega^2 S(\omega) d\omega \tag{21}$$

 $S(\omega)$ is the distribution of the frequency deviations from the center of the resonance, i.e., it is the lineshape function. An ensemble of spins in the sample with equal atomic positions and equal spatial orientations (polar coordinates $\{\theta, \varphi\}$ of the z axis of the tensor main frame) contributes to the spectrum at the two positions

235
$$\omega_{\text{aniso}} = \pm \frac{D}{2} \left[3\cos^2\theta - 1 + \eta\sin^2\theta\cos2\varphi \right]$$
 (22)

The whole line shape function is the sum over all individual lines which are here assumed to be δ functions:

$$S(\omega) = \int_{0}^{2\pi} d\varphi \int_{0}^{\pi} d\theta \sin\theta \, \delta(\omega - \omega_{\text{aniso}}(\theta, \varphi))$$
 (23)

Inserting eqns. (23) and (22) into eqn. (21) gives

$$M_2 = \frac{D_0^2}{5} \left(1 + \frac{\eta^2}{3} \right) \tag{24}$$

Now we can use the effective anisotropies and asymmetry parameters of the four models discuss above and obtain

$$M_2^{\text{(CH)}} = \frac{D_0^2}{5}; \qquad M_2^{\text{(CH-j)}} = \frac{7}{80}D_0^2; \qquad M_2^{\text{(CH2)}} = \frac{2}{5}D_0^2; \qquad M_2^{\text{(CH3)}} = \frac{1}{15}D_0^2;$$
 (25)

The two last expressions were obtained as averages between the corresponding expressions from both sum and difference tensors mentioned above. They are equal to the expressions for the second moments of multispin dipolar interactions; in the case of CH₃ the fast-rotation of this group was considered.

245 2.11 Parameter fit to experimental data

From the model functions and the exponential-damping approximation, the following expressions can be obtained which are immediately applicable for the data fit in the four respective cases mentioned above $(r := \tau_c^{-1})$:

$$F_1^{\rm IS}\left(D_{\rm res},\ \omega_{\rm r},\ r,\ t\right) = \exp\left\{-\frac{3}{5}\,\frac{3\pi D_{\rm res}^2\,r}{\omega_{\rm r}^3}\frac{t}{T_{\rm r}}\right\} \sum_{m=0}^{m_{\rm max}} C_m^{\rm IS}\left(\frac{D_{\rm res}}{\omega_{\rm r}}\right) \cdot \cos\left(2\pi m\frac{t}{T_{\rm r}}\right) \tag{26}$$

$$250 \quad F_{2}^{\text{IS-j}}(D_{\text{res}},\,\omega_{\text{r}},\,r,\,t) = \exp\left\{-\frac{21}{80}\,\frac{3\pi D_{\text{res}}^{2}\,r}{\omega_{\text{r}}^{3}}\,\frac{t}{T_{\text{r}}}\right\} \sum_{m=0}^{m_{\text{max}}} C_{m}^{\text{IS-j}}\left(\frac{D_{\text{res}}}{\omega_{\text{r}}}\right) \cdot \cos\left(2\pi m\frac{t}{T_{\text{r}}}\right) \tag{27}$$

$$F_3^{\rm IS2}(D_{\rm res}, \, \omega_{\rm r}, \, r, \, t) = \exp\left\{-\frac{6}{5} \, \frac{3\pi D_{\rm res}^2 \, r}{\omega_{\rm r}^3} \frac{t}{T_{\rm r}}\right\} \sum_{m=0}^{M_{\rm max}} C_m^{\rm IS2}\left(\frac{D_{\rm res}}{\omega_{\rm r}}\right) \cdot \cos\left(2\pi m \frac{t}{T_{\rm r}}\right) \tag{28}$$

$$F_4^{\text{CH3}}(D_{\text{res}}, \omega_{\text{r}}, r, t) = \exp\left\{-\frac{1}{5} \frac{3\pi D_{\text{res}}^2 r}{\omega_{\text{r}}^3} \frac{t}{T_{\text{r}}}\right\} \sum_{m=0}^{m_{\text{max}}} C_m^{\text{CH3}} \left(\frac{D_{\text{res}}}{\omega_{\text{r}}}\right) \cdot \cos\left(2\pi m \frac{t}{T_{\text{r}}}\right)$$
(29)

For each sample, data were recorded at different temperatures and different spinning speeds f_n . For each spinning speed, 8 data points were recorded along the indirect dimension t_1 at the times 0, $T_r/7$, $2T_r/7$, ..., T_r . The fitting procedure consisted of minimizing the summed square deviation χ^2 between data and model function

$$\chi_{\min}^2 := \min_{r>0, D_{\text{res}}>0} \chi^2 \quad \text{with} \quad \chi^2 := \sum_n \sum_{p=1}^8 \left[y_p^{(n)} - F(D_{\text{res}}, 2\pi f_n, r, t_p) \right]^2$$
 (30)

For obtaining information about the accuracy of the resulting parameters, the region in the $D_{\rm res}, r$ plane was considered where $\chi^2(D_{\rm res}, r) < 2 \, \chi^2_{\rm min}$.

3 Experimental

265

280

3.1 ¹³C solid-state NMR spectroscopy

One part of the 13 C solid-state NMR experiments (spectroscopy, HETCOR, solid-state APT, HMQC) was performed on a Bruker Avance NMR spectrometer operating at 75 MHz and 300 MHz for 13 C and protons, respectively, using a commercial 2.5 mm MAS NMR probe. 1 H \rightarrow 13 C CP spectra were recorded with a contact time of 4 ms; 15,000 scans with a recycle delay of 2 s were accumulated. The rf field strength applied during the CP contact and during the dipolar decoupling corresponds to a nutation frequency of 110 kHz.

For recording the directly excited ¹³C spectra, 1350 scans were accumulated with a recycle delay of 180 s. The decoupling field strength corresponded to a nutation frequency of 110 kHz.

During the HETCOR experiments, a contact time of 0.7 ms was used. 64 scans with an recycle delay of 2s were accumulated for each FID; 450 increments were executed. Ramped $^{1}H\rightarrow^{13}C$ cross-polarization (Pines et al., 1973; Metz et al., 1994) and SPINAL-64 proton decoupling (Fung et al., 2000) was applied; the rf field strength corresponded to a nutation frequency of 110 kHz.

For recording the solid-state ${}^{1}\text{H}^{-13}\text{C}$ APT spectra, we used for the CP excitation the same parameters as for the CPMAS experiments mentioned above, i.e. contact time 4 ms and rf field strength corresponding to 110 kHz. 20,000 signals were accumulated with a recycle delay of 2 s. ${}^{1}\text{H}^{-13}\text{C}$ through-bond HMQC spectra were obtained with 1600 scans per FID and 70 increments.

DIPSHIFT experiments were performed on a Bruker Avance III spectrometer operating at 100 MHz and 400 MHz for 13 C and protons, respectively, with a commercial 4 mm MAS NMR probe. The spinning speed was varied as described in the results section. The 1 H nutation frequency was 60.5 kHz which required an offset of 42.8 kHz for the Lee-Goldburg decoupling within these experiments. For establishing the CP, the 13 C rf field strength was set to the effective proton rf field of 74.1 kHz. Between 3200 and 6400 scans per t_1 value were recorded with recycle delays of 2 s (25°C) and 3 s (-15°C), resp. The temperature inside

the rotor was calibrated using the ²⁰⁷Pb chemical shift of lead nitrate as a temperature reference (Ferguson and Haw, 1995). Adamantane served as an external shift standard.

285 3.2 Synthesis of the linker and of PIZOF-10

The PIZOFs were obtained through the standard process described for PEPEP-PIZOFs by Schaate et al. (2011). For the synthesis of PIZOF-10, ZrCl₄ (0.080 g, 0.34 mmol), HO₂C[PE-P(O(CH₂CH₂O)₃CH₃, O(CH₂CH₂O)₃CH₃)-EP]CO₂H (0.34 mmol) and benzoic acid (1.256 g, 10.29 mmol) as modulator were dissolved in 20 mL DMF. The solution was heated in a tightly capped 100 mL glass flask to 120 °C in an oven for 4 days. The precipitate was isolated from the mother liquor via centrifugation and washed by immersion in DMF for 30 min followed by centrifugation. The immersion and centrifugation steps were repeated with ethanol. The product was dried at reduced pressure and the obtained dry powder was submitted to Soxhlet extraction with ethanol for 24 h. The mother liquor was again filled into a glass flask and heated to 120 °C. An additional fraction of product was obtained within 24 hours, which was isolated and washed as described for the first crop. All fractions were merged.

295 4 Results

290

300

305

310

4.1 Spectral assignment of the ¹³C spectra

The solid-state ¹³C NMR spectra of PIZOF-2, PIZOF-10, and PIZOF-11 are well resolved. This allowed us to obtain almost complete ¹³C NMR signal assignment for these three samples (see Fig. 5, Figures S1 and S2 (Supplementing Information) and Table 2). Rough assignment of the solid-state ¹³C lines could be obtained already by a comparison to the liquid-state ¹³C NMR spectra of the dicarboxylic acid (used for the synthesis of PIZOF-10) in DMSO-d₆. We observed very similar chemical shifts for most of the detected signals. Significant differences of the order of ca. 5 ppm occur for the carboxylate group (10) and the aromatic carbon (8) directly bound to (10). This is probably caused by the proximity to the metal atom. The signal assignment is further supported on the interpretation of liquid-state DEPT 135 as well as solid-state APT spectra (Fig. 5). Both methods are able to distinguish differently protonated carbons: In DEPT 135 spectra, the signals of CH and CH₃ appear positive, whereas CH₂ groups cause negative resonances. Quaternary carbons do not give any signal in DEPT 135. In analogy to the routine liquid-state APT method, for a certain internal delay, CH and CH₃ groups produce negative signals while the resonances of quaternary carbons and CH₂ groups are positive. Distinction between quaternary carbons and CH₂ is also possible based on the significantly higher intensity of quaternary carbon signals compared to the signals of CH₂. The signal assignments summarized in Table 2 are further corroborated by ¹H-¹³C HETCOR and ¹H-¹³C HMOC spectra, see Fig. 6.

Comparing the solid-state ¹³C spectra of the different PIZOFs we found the most relevant differences between the spectra of the different PIZOFs in the CH₂ region, showing the different kinds of sidechains, and in the aromatic region between 111 and 118 ppm. Whereas the PIZOF-2 spectrum simply contains the OCH₃ resonance, no complete resolution is found for the different aliphatic carbon positions in the chains except PIZOF-11 at room temperature. Further, the resonance of the CH of

Signal	δ [ppm]	Structural group		
1	58	OCH ₃		
2	71	OCH ₂ CH ₂ O		
3	89.5 / 96.5	C≡C		
4	115	$\underline{\underline{C}}^{ar}C \equiv C \text{ (ortho to O)}$		
5	117	C ^{ar} (ortho to O)		
6	127	C ^{ar} H (para to CO ₂)		
7	131	C ^{ar} H		
8	134	$\underline{C}^{ar}CO_2H$		
9	155	CarO		
10	171	CO_2H		

Table 2. Assignment of the solid-state ¹³C NMR signals of PIZOF-10.

the central benzene ring overlaps with the line of CarC≡C. They could be separated for PIZOF-10 and PIZOF-11, see below.

315 For PIZOF-2, however, a complete overlap of both resonances occurs which does not permit a DIPSHIFT analysis of the central-ring CH at all.

4.2 Indication for anisotropic motions of the sidechains

Figure 7 shows the directly excited ¹³C MAS NMR spectra as well as ¹³C CP MAS NMR spectra measured with 4 ms contact time for the three samples under study. If the long side chains in PIZOF-10 and PIZOF-11 were liquid-like and would move isotropically, the ¹H-¹³C CP efficiency should be very low or even zero as compared to the ¹³C signals of the other framework carbons. The existence of rather strong aliphatic lines implies interpretations either as a consequence of slow motion of the chains, or as indeed fast but spatially restricted reorientation. The latter leads, even for very short correlation times, to a non-zero residual dipolar coupling, see above, which enables cross polarization even in the case of a fast motion. For distinguishing between these cases the DIPSHIFT method was used.

325 4.3 Line decompositions

320

330

As explained above, we focus on the signals of protonated carbons for the DIPSHIFT data. This concerns the CH of the lateral rings (overlapping at about 130 ppm with the resonances of some quarternary C) and the CH of the central ring. In PIZOF-10 and -11, the related lines overlap partially with the line of the quarternary C bound to the acetylenic C (in PIZOF-2 there is a complete overlap which could not resolved, see above). The sidechain resonances in PIZOF-10 and -11 feature some overlap; their resolution could deliver information about the order parameter gradient along the side chain. It turns out that, despite the enhanced uncertainty because of decomposition, well-defined plots of intensity vs. $t_1/T_{\rm r}$ were obtained.

Concerning the aliphatic region of PIZOF-11, whereas at 30 °C five CH_2 lines are well resolved, at -15 °C there is a strong overlap because of increased line broadening. Fig. 9 shows a decomposition in Lorentzian components. The lines could be

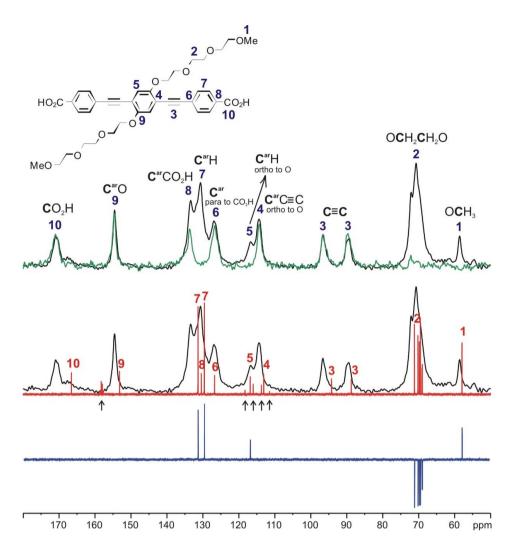


Figure 5. Signal assignment for the 13 C NMR spectrum of the linker of PIZOF-10 based on the interpretation of 13 C CP MAS NMR spectrum (black), 13 C solid-state APT NMR spectrum (green), 1 H broadband proton-decoupled liquid-state (DMSO-d6), 13 C NMR spectrum (red), and liquid-state (DMSO-d6) DEPT 135 13 C NMR spectrum (blue). The signals marked with \uparrow are assigned to trifluoroacetic acid, which was used in the last step of the synthesis of the linkers.

assigned to the atomic positions by means of the predictions of ACD software (Advanced Chemistry Development Inc., 2017).

Most lines at -15 °C can be assigned immediately to corresponding lines of the 30 °C spectrum with one exception: The central resonance (δ position) seems to split at lower temperature into two overlapping components. The position of one of them corresponds to δ in the 30 °C spectrum, the other in a distance of about -1.2 ppm is denoted here as δ_1 . It is possible that different conformations (for example trans and gauche) along the chains are frozen-in at -15 °C whereas faster motions at 30 °C average them, leading to an average chemical shift.

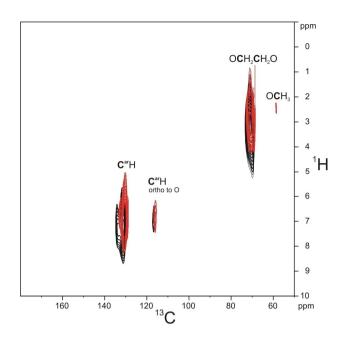


Figure 6. Comparison of the ¹H-¹³C HETCOR spectrum of PIZOF-10 measured at short contact time (0.7 ms, black) and the ¹H-¹³C HMQC spectrum (red).

In some contrast, the signal assignment for the aliphatic carbons (signal 2 in Fig. 5 and in table 2) of PIZOF-10 is not fully clear. From a comparison with a prediction of isotropic chemical shifts obtained by the ACD software, we expect the resonances of carbons 2b, 2c, 2d, 2e within a region of 0.7 ppm, carbon 2a to be shifted by about 1.2 ppm with respect to the center of the former group of resonances, and carbon 2f to be shifted by about -0.6 ppm. (For the sub-numbering of the aliphatic carbons see Fig. 10). Taking into account that the solid-state resonances might deviate non-systematically from the solution-based shifts, we could attain a coarse assignment of the -15 °C lines to the following carbon positions: A to 2a, B to 2b, 2c, 2d and 2e, C to position 2f. For the five components of the 25°C spectrum, the assignment however will remain unknown at this stage. Typical solid-state NMR phenomena like conformational differences (e.g. trans/gauche) could generate additional shifts. A possible assignment will be given in the discussion section.

The separation of the ring-CH resonances from overlapping quarternary C resonances is always straightforward. Further lineshape decompositions can be found in the Supplementary Material.

4.4 Evaluation of the CP buildup curves

Comparisons of the signal intensities for PIZOF-10 and PIZOF-11 reveal similar CP efficiencies for most side-chain carbon signals as for the other ¹³C signals of protonated carbons in the framework – except for the chain ends, where the CP efficiency significantly drops (Figure 7).

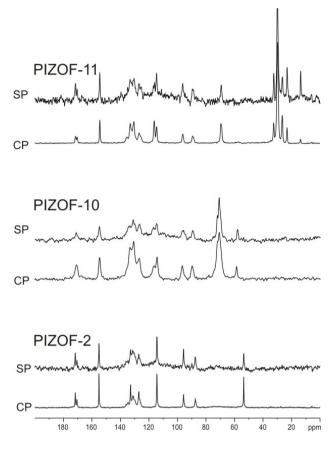


Figure 7. Comparison of directly excited ¹³C MAS NMR spectra and ¹³C CP MAS NMR spectra (4 ms contact time) of PIZOF-2, PIZOF-10 and PIZOF-11.

In CP experiments, several parameters influence the rate and efficiency of polarization transfer, in particular (i) the longitudinal relaxation time of the protons in the rotating frame $T_{1\rho}$, (ii) the number of neighboring protons and their distances from the 13 C nuclei, and (iii) the mobility of the nuclei. To investigate the spin polarization transfer, CP buildup curves are measured (Mehring, 1983). 1 H \rightarrow 13 C CP MAS spectra are recorded with different contact times (here between 0.35 and 10 ms) and the intensities of the individual signals are plotted versus the contact time. Protons directly bound to the carbon lead to fast and efficient CP buildup and hence to short buildup time constants T_{CH} , whereas carbons without directly bound protons, e.g., larger distances to protons show longer CP buildup times. Thermal motions result in a less efficient CP buildup and result in longer CP buildup times T_{CH} (Schulze et al., 1990). CP buildup curves for Pizof-10 are shown in the SI, the time constants T_{CH} obtained from this are shown in Figure 8 and Table 3.

The fastest CP buildups are observed for aromatic CH groups (5, 7) and CH₂O groups (2). It is interesting to compare the CP buildup time constants for protonated carbon positions located at the framework (CH groups of the lateral rings 5, 7) with the time constants for the CH₂ groups of the side chains (2). If the rigidity of the framework and the sidechains were identical,

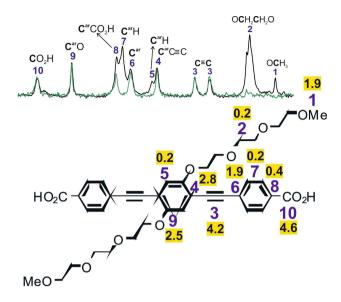


Figure 8. ¹H-¹³C CP buildup time constants (in units of ms) for selected ¹³C signals of PIZOF-10. In the upper part, the ¹³C CPMAS spectrum (black) as well as the solid-state APT spectrum (green) are shown.

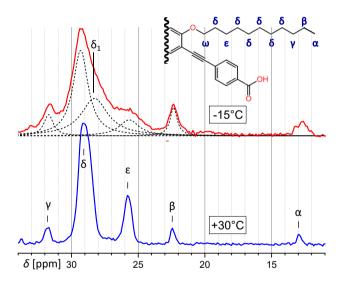


Figure 9. Comparison of the aliphatic regions of 13 C spectra of PIZOF-11 at different temperatures. Whereas at 30°C different positions are well separated from another, it is not the case at -15°C. The decomposition into a number of Lorentzian lines is shown. One component of this decomposition (δ_1) seems to have no counterpart at 30 °C. (ω -CH₂ is at 69 ppm and not visible here.)

 T_{CH} of CH₂ would be shorter than for CH. In our experiments, the values for T_{CH} of CH₂ and CH are similar. This indicates that the sidechains (2) are slightly more flexible than the framework (5, 7) but still relatively rigid. Because the signals of the different side-chain positions are not resolved (2), the time constant cannot be determined for the different CH₂ groups.

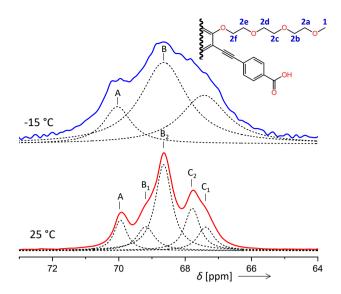


Figure 10. Comparison of the aliphatic regions of ¹³C spectra of PIZOF-10 at different temperatures. Whereas at 25°C five components could be resolved (bottom), at -15°C only three were detected (top). The numbering of the carbon positions serves to discussions in subsection "line decompositions".

Signal	1	2	3	4	5	6	7	8	9	10
Group	OCH ₃	OCH_2	C≡C	C^{ar}	$C^{ar}H$	C^{ar}	$C^{ar}H$	C^{ar}	CarO	СООН
T_{CH} in ms	1.9	0.2	4.2	2.8	0.2	1.9	0.2	0.4	2.5	4.6

Table 3. Buildup time constants T_{CH}^{\dagger} values obtained for the ^{13}C signals in PIZOF-10 (for the corresponding buildup curves, see SI).

The DIPSHIFT measurements however allow further interpretations. Theoretically, an immobile CH₃ group should have the shortest time T_{CH} compared to all other carbons in PIZOF-10. The terminal CH₃ at the end of the side chains (1), however, exhibits a rather long T_{CH} value. This is likely due to the combined influence of methyl group rotations and increased mobility of the chain end. It can, therefore, be concluded that the side chains are far from showing a liquid-like behavior. Obviously, they are relatively ordered and fixed in space due to interactions among themselves and/or with the framework. This is in agreement with previous ¹³C CP MAS NMR studies, e.g., of *n*-alkyl silanes bound to silica surfaces (Sindorf and Maciel, 1983) showing that (i) significant CP transfer occurs for all carbon atoms and (ii) the CP efficiency decreases with increasing distance from the surface, i.e., from the anchoring point of the chain.

4.5 Evaluation of the DIPSHIFT curves

DIPSHIFT data and model functions with fitted parameters D_{res} and r of the methyl carbon in PIZOF-2 are shown in Fig. 11.

380 DIPSHIFT curves and mean-square deviation surfaces for other carbon positions which were evaluated can be found in the supplementary material.

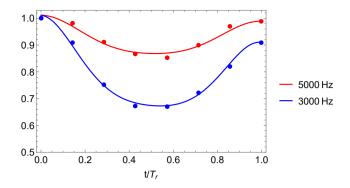


Figure 11. DIPSHIFT curves of OCH₃ of PIZOF-2 at 30 °C for different spinning frequencies. The solid lines show model function 4 with values for the parameters D_{res} and r_{c} which give the best fit to the experimental data for both spinning rates.

Numerical values for $D_{\rm res}$ and r are summarized in Tables 4, 5 and 6 for the respective samples. The last columns each contain the order parameters $S=D_{\rm res}/D_0$. C–H distances are between 1.09 and 1.10 Å which gives a coupling constant reduced by the Lee-Goldburg scaling factor $D_{\rm LG}=D_0/\sqrt{3}=(13.28\pm0.18)$ kHz. The resulting uncertainty of about 1.4 % is smaller than the experimental uncertainties and therefore influences the uncertainty of the order parameter only weakly.

Eine Inhomogenität des HF-Feldes kann jedoch den Lee-Goldburg-Skalierungsfaktor (Lee and Goldburg, 1965) beeinflussen. Die DIPSHIFT-Daten stellen dann Überlagerungen der Daten der einzelnen Probenorte dar. Die Kalibrierung des Experimentes basiert auf der über die Probe Zitat: (Wurl et al., 2023) Das kann zu zwei verschiedenen Veränderungen führen:

1. An manchen Orten in der Probe ist die Abweichung von der LG-Bedingung so groß, dass die homonukleare dipolare Wechselwirkung innerhalb des Protonenspinsystems nicht mehr ausreichend unterdrückt wird. Dadurch ist eine etwas stärkere Dämpfung des Rotationsechos zu erwarten. Dies wird jedoch nicht in die weitere Auswertung der Daten einbezogen; 2. Eine Variation des LG-Faktors führt zu einer Variation von DLG, das anstelle von D0 in die Gleichungen (31) bis (32) einzusetzen ist. Das bedeutet, dass die zentralen Minima der entsprechenden Kurven unterschiedlich hoch sind. Diese überlagern sich jedoch zu einer Gesamtkurve, die in sehr guter Näherung gleich derjenigen ist, die sich für die mittlere HF-Feldstärke ergibt. Auf letztere ist das Experiment kalibriert worden DIPSHIFT-Kurven mit unterschiedlicher Höhe des zentralen Minimums. Diese Variation ist in der Umgebung von w3 jedoch linear, wie eine Taylorentwicklung der Funktion zeigt.

5 Discussion

385

390

395

400

The evolution of the 13 C magnetization during a 1 H- 13 C cross-polarization experiment is characterized for short times ($\sim D_{\rm res}^{-1}$) by powder-averaged oscillations determined by the (residual) dipolar coupling. For longer times, however, spin diffusion within the proton system will be more and more important; it provides a re-polarization of those protons which are close to 13 C and have been depolarized during CP. Both phenomena are expected to be slowed down by thermal motion.

The $T_{\rm CH}$ values corresponding to the long-time buildup indicate an increased mobility towards the end of the side chains. With regards to the related thermal motion we can distinguish two cases: (i) Slow or intermediate nearly isotropic motion,

Carbon position	Temp.	fit model	$D_{ m res}[{ m kHz}]$	$r[\text{ms}^{-1}]$	$\chi^2_{ m min}$	S
CH ₃	+30°C	4	5.8 ±0.5	0.4 ±0.4	0.00395	0.436 ± 0.028
	-15°C	4	6.47 ± 0.37	0.68 ± 0.15	0.00147	0.486 ± 0.038
CH (terminal ring)	-15°C	1	8.3 ±1.0	$0.4_{-0.3}^{+0.5}$	0.0516	0.624 ± 0.075
		2	12.6 ±1.5		0.0528	0.947 ± 0.113

Table 4. Residual dipolar couplings, damping constants, minimum mean-square deviations and order parameters for methyl carbons and for protonated sidering carbons in PIZOF-2. For the ring CH, two different fit models were applied, see text.

Carbon position	Temp.	fit model	$D_{ m res}$ /kHz	$r [\mathrm{ms}^{-1}]$	$\chi^2_{ m min}$	S
CH ₂ A	-15°C	3	2.9 ±0.5	$3.3_{-3.3}^{+12}$	0.0225	0.218 ± 0.038
	25°C	3	2.7 ± 0.6	$1.3 \begin{array}{c} +2.6 \\ -1.3 \end{array}$	0.00529	0.201 ± 0.045
CH ₂ B ₁	25°C	3	3.4 ±0.4	3. $^{+5.6}_{-3}$	0.00530	0.256 ± 0.030
CH ₂ B	-15°C	3	3.11±0.25	$0.8_{\ -0.7}^{\ +1}$	0.00767	0.234 ± 0.023
CH_2 B_2	25°C	3	2.08 ± 0.35	$0.9_{\ -0.9}^{\ +6}$	0.0296	0.156 ± 0.038
CH_2 C_2	25°C	3	4.64±0.3	$1.4 \begin{array}{c} +1.6 \\ -1.2 \end{array}$	0.0052	0.349 ± 0.023
CH ₂ C	-15°C	3	8.2 ±0.7	$1.1 \begin{array}{c} +1.2 \\ -0.8 \end{array}$	0.0232	0.614 ± 0.053
CH_2 C_1	25°C	3	6.4 ± 0.5	$1.9_{\ -1.4}^{\ +2}$	0.0135	0.478 ± 0.038
	-15°C	1	10.9 ±1.0	$0.8 \begin{array}{l} +1.0 \\ -0.6 \end{array}$	0.050	0.823 ± 0.075
Middle ring		2	16.6 ± 1.5	". "	0.051	1.245 ± 0.113
	25°C	1	10.7 ± 0.9	$0.4 \begin{array}{l} +0.8 \\ -0.4 \end{array}$	0.0492	0.805 ± 0.068
		2	15.6 ±2.5	". "	0.169	1.173 ± 0.188
	-15°C	1	10.2 ± 0.9	$0.5_{\ -0.5}^{\ +0.8}$	0.0283	0.767 ± 0.068
Terminal ring	25°C	1	8.5 ±0.9	$0.21^{+0.5}_{-0.2}$	0.0637	0.639 ± 0.068
		2	12.8 ± 1.5	". "	0.0649	0.962 ± 0.113

Table 5. Residual dipolar couplings, damping constants, minimum mean-square deviations and order parameters for some carbon positions and for components of methylene resonances in PIZOF-10. Again, for the ring CH, two different fit models were applied, see text.

Line assignment	Temp.	fit model	$D_{\rm res}$ /kHz	$r [\mathrm{ms}^{-1}]$	$\chi^2_{ m min}$	S
	-15°C	3	$1.5 \begin{array}{c} +0.3 \\ -0.5 \end{array}$	$0.5 \begin{array}{c} +4 \\ -0.5 \end{array}$	0.0389	$0.11^{+0.024}_{-0.04}$
β -CH $_2$	25°C	3	1.0 ± 0.5	$6.4 ^{+50}_{-6.0}$	0.0128	$0.075{}^{+0.030}_{-0.045}$
	30°C	3	$1.2_{-0.4}^{+0.3}$	$0.3 ^{+3.5}_{-0.3}$	0.0238	$0.09^{+0.02}_{-0.03}$
	-15°C	3	1.88± 0.5	$0.50 \begin{array}{l} +3.3 \\ -0.5 \end{array}$	0.0630	0.14 ± 0.04
γ -CH $_2$	25°C	3	$1.28 \!\pm 0.3$	$3.6 ^{+6}_{-3.6}$	0.0097	0.10 ± 0.03
	30°C	3	$1.6\ \pm0.4$	$0.3 ^{+2}_{-0.3}$	0.0324	$0.12^{+0.02}_{-0.03}$
	-15°C	3	$2.5\ \pm0.4$	$0.5 ^{+1.1}_{-0.5}$	0.0347	0.19 ± 0.03
δ -CH $_2$	-15°C	3	$5.0\ \pm0.7$	$0.23 \begin{array}{l} +0.2 \\ -0.1 \end{array}$	0.0367	0.37 ± 0.06
	25°C	3	$1.94 \!\pm 0.16$	$1.4 ^{+0.8}_{-0.5}$	0.0048	0.15 ± 0.01
	30°C	3	$2.33 \!\pm 0.25$	$0.36_{\ -0.25}^{\ 0.4}$	0.0246	0.17 ± 0.02
	-15°C	3	$3.5\ \pm0.5$	$0.31 \begin{array}{l} +0.8 \\ -0.3 \end{array}$	0.0374	0.26 ± 0.034
ε -CH $_2$	25°C	3	2.51 ± 0.11	0.48 ± 0.25	0.0030	0.19 ± 0.01
	30°C	3	$2.44 \!\pm 0.2$	$0.34 \begin{array}{l} +0.5 \\ -0.3 \end{array}$	0.0129	0.18 ± 0.015
	-15°C	3	7.1 ± 0.9	$0.8 ^{+0.9}_{-0.5}$	0.1040	0.53 ± 0.068
ω -CH $_2$	25°C	3	$5.5\ \pm0.3$	0.40 ± 0.16	0.0150	0.41 ± 0.02
	30°C	3	5.55 ± 0.45	$0.22 \ ^{+0.13}_{-0.09}$	0.0247	0.42 ± 0.03
	-15°C	1	$9.9_{-0.9}^{+1.1}$	$0.13 \begin{array}{c} +0.9 \\ -0.13 \end{array}$	0.1250	$0.74^{+0.090}_{-0.07}$
		2	14.4 ± 3.1	." "	0.1610	1.1 ± 0.02
Middle ring	25°C	1	$10.0\ \pm0.4$	0.34 ± 0.3	0.0053	0.76 ± 0.03
		2	$15.2\ \pm0.6$." "	0.0055	1.14 ± 0.05
	30°C	1	$9.1\ \pm1.1$	$0.16 ^{ +0.64}_{ -0.16}$	0.0567	0.68 ± 0.08
		2	$13.7\ \pm1.8$." "	0.0580	1.03 ± 0.14
	-15°C	1	9.9 ±1.9	$0.13 \begin{array}{c} +1.9 \\ -0.13 \end{array}$	0.1250	0.75 ± 0.14
Terminal ring	25°C	1	$9.4 \begin{array}{l} +1.25 \\ -1.1 \end{array}$	$0.066^{+0.3}_{-0.066}$	0.1530	0.71 ± 0.09
	30°C	1	$10.8\ \pm1.3$	$0.27 \begin{array}{l} +0.55 \\ -0.27 \end{array}$	0.0729	0.80 ± 0.10

Table 6. Residual dipolar couplings, damping constants, minimum mean-square deviations and order parameters for some carbon positions in PIZOF-11. Again, for the ring CH, two different fit models were applied, see text.

which would cause a loss of CP efficiency upon speeding up; (ii) Fast anisotropic motion which does not hamper CP buildup even in the fast limit because of the residual dipolar coupling. The latter enables both oscillatory behaviour in the CH systems at short times and spin-diffusion in the proton system at long times. The DIPSHIFT results provide a distinction between these two options. The first case would lead to strongly damped rotational echoes in the FID, see above; a re-increase in the second half of the DIPSHIFT curve would not occur. The DIPSHIFT signals obtained for the PIZOF samples, however, show a clear recovery of the rotational echo reaching almost the initial FID intensity.

In most cases investigated here, the residual dipolar couplings are essentially smaller than the value which would occur for immobile structural groups. Consequently, thermal motion that effectively averages the dipolar interactions must be present. This motion must be much faster than the strength of carbon-proton dipolar coupling, i.e. the correlation times must be shorter than 10^{-5} s (in the intermediate region in a range 10^{-5} s ... 10^{-3} s, the motion would lead to a strong damping of the rotational echoes). The rotational echo after one rotation period is slightly damped, but in no case to less than 70% of the initial signal. That means that fast motion reduces the apparent dipolar coupling and the existence of a rather slow motion with correlation times of 2×10^{-3} s causing the observed weak damping of the rotational echoes for room temperature as well as for -15° C. This slow motion leads to a further averaging of the dipolar interaction, but just at times which are much longer than the duration of the DIPSHIFT modulation period.

410

415

420

425

430

435

The sidechain order parameter could be estimated for different positions on the basis of our line decomposition, reminding that only for PIZOF-11 at 25 °C, the aliphatic lines are well resolved. Besides the δ_1 component occurring at -15°C only (see Fig. 9), all low-temperature components of the devonvolution could be assigned to the well-separated room temperature lines and therefore also to carbon positions. A gradient of the order parameter along the chain could be detected, see Fig. 12. On this basis, we can give a possible explanation for the occurrence of the δ_1 component. The value of its order parameter, which is placed between the S values of ε carbons and ω carbons, implies an assignment to the carbon being placed next to the ω carbon. At room temperature, its resonance is part of the signal group of the δ carbons. Perhaps because of conformational effects, it is shifted towards higher ppm values at -15°C.

The order parameters of the sidechains in PIZOF-10 are shown in Fig. 13. Following the liquid-state assignment (see "Line decompositions"), component A was assigned to pos. 2a, component C was assigned to pos. 2f. The order parameter of the carbon at position 2f is clearly larger than that of the remaining part of the side chain. This phenomenon occurring also in PIZOF-11 can be understood by the proximity of these carbons to the more rigid central rings, see below. The value of the order parameter of component C_2 strongly suggests an assignment of this component to position 2e. The order parameter of component C_2 strongly weak yet beyond the limits of uncertainty. Hence, an assignment of this component to carbon position 2d is likely to some degree.

A comparison of the different side chains groups linked via O to the central rings shows that the order parameters of PIZOF-10 and of PIZOF-11 are equal within experimental uncertainty. However, in PIZOF-2 at -15 °C, the bond order parameter of the methyl group is clearly smaller than that of the ω -CH₂ of both other PIZOFs, reminding that we have considered the fast rotation around the methyl symmetry axis in the fit. This indicates that there is a fast motion of the methyl axis itself which takes place in a range of angles which is of larger amplitude than in the case of the ω methylenes in PIZOF-10 and PIZOF-11.

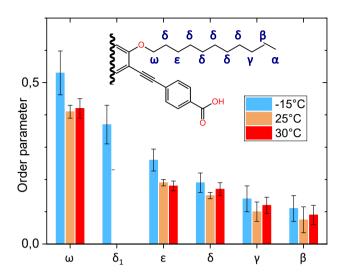


Figure 12. Graphical representation of the order parameter gradient along the side chains of PIZOF-11. The label " δ_1 " marks the position in the chain where the origin of this line is assumed; see text.

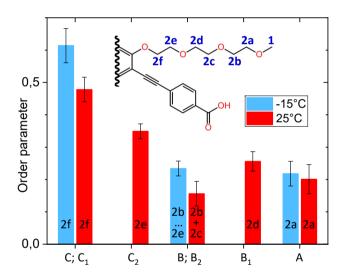


Figure 13. Graphical representation of the order parameters for the different components of the methylene line in PIZOF-10.

The order parameters of the central rings are graphically compared in Fig. 14. The PIZOF-2 spectrum did not allow for a separation of the corresponding line from a completely overlapped group of signals. Hence, we now deal with the two other samples only. For PIZOF-10, similar order parameters (0.74 and 0.68 for -15°C and 30°C, resp.) as for PIZOF-11 (0.82 and 0.80 for the same temperatures) were determined. We observe that the first ones are slightly smaller but not beyond the limits of experimental uncertainty. 180° flips of the rings are not expected because of the linked sidechains. Indeed, an attempt of

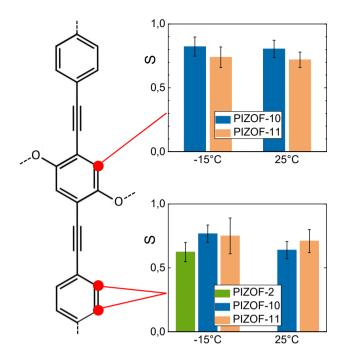


Figure 14. Graphical representation of the order parameters for the protonated carbons in the middle ring (top) and terminal rings (bottom).

evaluating the DIPSHIFT curves by model function 2 (for 120° jumps of the CH bonds) failed; it delivered unrealistically high values for the residual dipolar coupling.

With regards to the terminal rings, flips could also not be detected; the fit attempt led to $D_{\rm res}$ values which would be larger than those expected for rigid molecular parts. Evidence of such rapid motion would only be given if $D_{\rm res} < D_{\rm LG}$ had been found to be out-side the error limits. This concerns also slow flips, as this would lead to a larger T_2 damping of the rotational echo. An order parameter < 1 has thus to be explained by fast small-angle motions. For the central ring, π flips have a very small likelihood because of the attached side chains.

6 Conclusions

450

Long aliphatic and ethyleneglycol sidechains of the PIZOF samples were shown to exhibit a gradient of anisotropy of motion. Not only the terminal methyl groups but also the methylene groups close to the CH₃ are subject to fewer restrictions than the inner CH₂ groups. The carbons closest to the linker backbone are subject to the strongest motional restrictions.

"Restriction" in our senses does not concern the speed of the motion but the degree of anisotropy. Assuming that this anisotropic motion would proceed as fluctuations of the CH₂ plane normals or CH₃ rotation axes within a cone with defined opening angle, this angle would be the larger, the smaller the order parameter is. This is reminiscent of the dynamics in

nematic liquid crystals; overall we observe orientational restrictions to different degrees despite rather short correlation times. The difference to liquid crystals is found in the existence of long-range order of the chains of the latter.

460 7 cos-Fourier coefficients

7.1 Case 1: Ensemble of rigid IS spin pairs

$$C_{1}^{\text{IS}} = \frac{2}{15} \left(\frac{D_{0}}{\omega_{r}}\right)^{2} - \frac{17}{1260} \left(\frac{D_{0}}{\omega_{r}}\right)^{4} + \frac{131}{205920} \left(\frac{D_{0}}{\omega_{r}}\right)^{6} - \frac{12583}{705729024} \left(\frac{D_{0}}{\omega_{r}}\right)^{8} + \frac{356981}{1072708116480} \left(\frac{D_{0}}{\omega_{r}}\right)^{10} - \frac{25270187}{5693604618240000} \left(\frac{D_{0}}{\omega_{r}}\right)^{12}$$

$$(31)$$

$$C_2^{\text{IS}} = \frac{1}{60} \left(\frac{D_0}{\omega_{\rm r}}\right)^2 + \frac{1}{720} \left(\frac{D_0}{\omega_{\rm r}}\right)^4 - \frac{2983}{23063040} \left(\frac{D_0}{\omega_{\rm r}}\right)^6 + \frac{63863}{14114580480} \left(\frac{D_0}{\omega_{\rm r}}\right)^8 - \frac{268843}{2860554977280} \left(\frac{D_0}{\omega_{\rm r}}\right)^{10} + \frac{56352451}{42295348592640000} \left(\frac{D_0}{\omega_{\rm r}}\right)^{12}$$

$$(32)$$

$$C_3^{\text{IS}} = \frac{1}{1260} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{397}{8648640} \left(\frac{D_0}{\omega_r}\right)^6 + \frac{353}{235243008} \left(\frac{D_0}{\omega_r}\right)^8 - \frac{17669}{536354058240} \left(\frac{D_0}{\omega_r}\right)^{10} + \frac{601529}{1174870794240000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(33)$$

465 7.2 Case 2: Spin pairs undergoing fast 2-site jumps

See equation (9):

$$C_0^{\text{IS-j}} = 1 - \frac{21}{320} \left(\frac{D_0}{\omega_{\text{r}}}\right)^2 + \frac{1589}{737280} \left(\frac{D_0}{\omega_{\text{r}}}\right)^4 - \frac{1887217}{47233105920} \left(\frac{D_0}{\omega_{\text{r}}}\right)^6 + \frac{11118847}{23492397367296} \left(\frac{D_0}{\omega_{\text{r}}}\right)^8 - \frac{757129037}{194773330899763200} \left(\frac{D_0}{\omega_{\text{r}}}\right)^{10} + \frac{9126896358637}{389583325014754590720000} \left(\frac{D_0}{\omega_{\text{r}}}\right)^{12}$$

$$(34)$$

$$C_{1}^{\text{IS-j}} = \frac{7}{120} \left(\frac{D_{0}}{\omega_{r}}\right)^{2} - \frac{119}{46080} \left(\frac{D_{0}}{\omega_{r}}\right)^{4} + \frac{321983}{5904138240} \left(\frac{D_{0}}{\omega_{r}}\right)^{6} - \frac{4601521}{6607236759552} \left(\frac{D_{0}}{\omega_{r}}\right)^{8} + \frac{193149817}{32137599598460928} \left(\frac{D_{0}}{\omega_{r}}\right)^{10} - \frac{46589311577279}{1241796848484530257920000} \left(\frac{D_{0}}{\omega_{r}}\right)^{12}$$

$$(35)$$

$$C_{2}^{\text{IS-j}} = \frac{7}{960} \left(\frac{D_{0}}{\omega_{r}}\right)^{2} + \frac{49}{184320} \left(\frac{D_{0}}{\omega_{r}}\right)^{4} - \frac{257057}{18893242368} \left(\frac{D_{0}}{\omega_{r}}\right)^{6} + \frac{32474753}{132144735191040} \left(\frac{D_{0}}{\omega_{r}}\right)^{8} - \frac{1107477091}{428501327979479040} \left(\frac{D_{0}}{\omega_{r}}\right)^{10} + \frac{91276751182213}{4967187393938121031680000} \left(\frac{D_{0}}{\omega_{r}}\right)^{12}$$

$$(36)$$

$$C_3^{\text{IS-j}} = \frac{7}{46\,080} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{14\,123}{7\,084\,965\,888} \left(\frac{D_0}{\omega_r}\right)^6 - \frac{76\,733}{11\,012\,061\,265\,920} \left(\frac{D_0}{\omega_r}\right)^8 + \frac{30\,099\,811}{80\,343\,998\,996\,152\,320} \left(\frac{D_0}{\omega_r}\right)^{10} - \frac{587\,419\,421\,473}{137\,977\,427\,609\,392\,250\,880\,000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(37)$$

7.3 Case 3: Spin triples IS₂

$$C_0^{\text{IS2}} = 1 - \frac{3}{10} \left(\frac{D_0}{\omega_r}\right)^2 + \frac{227}{4536} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{49471}{9729720} \left(\frac{D_0}{\omega_r}\right)^6 + \frac{293281}{840647808} \left(\frac{D_0}{\omega_r}\right)^8 - \frac{286311167}{16662021667200} \left(\frac{D_0}{\omega_r}\right)^{10} + \frac{142610164787}{225135039577536000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(38)$$

$$C_1^{\text{IS2}} = \frac{4}{15} \left(\frac{D_0}{\omega_r}\right)^2 - \frac{34}{567} \left(\frac{D_0}{\omega_r}\right)^4 + \frac{2843}{405405} \left(\frac{D_0}{\omega_r}\right)^6 - \frac{17689}{33776028} \left(\frac{D_0}{\omega_r}\right)^8 + \frac{2272579}{83310108336} \left(\frac{D_0}{\omega_r}\right)^{10} - \frac{258076147}{246858596028000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(39)$$

$$C_2^{\text{IS2}} = \frac{1}{30} \left(\frac{D_0}{\omega_r}\right)^2 + \frac{1}{162} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{2437}{1297296} \left(\frac{D_0}{\omega_r}\right)^6 + \frac{966239}{4728643920} \left(\frac{D_0}{\omega_r}\right)^8 - \frac{2084551}{158685920640} \left(\frac{D_0}{\omega_r}\right)^{10} + \frac{6874356527}{11938979371536000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(40)$$

$$C_3^{\text{IS2}} = \frac{2}{567} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{229}{1459458} \left(\frac{D_0}{\omega_r}\right)^6 - \frac{9379}{394053660} \left(\frac{D_0}{\omega_r}\right)^8 + \frac{224699}{69425090280} \left(\frac{D_0}{\omega_r}\right)^{10} - \frac{19307643899}{98496579815172000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(41)$$

7.4 Case 4: Spin quartetts IS₃

$$C_0^{\text{IS3}} = 1 - \frac{1}{20} \left(\frac{D_0}{\omega_r}\right)^2 + \frac{227}{77760} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{67283}{560431872} \left(\frac{D_0}{\omega_r}\right)^6 + \frac{12503873}{3919820636160} \left(\frac{D_0}{\omega_r}\right)^8 - \frac{122411059}{2116703143526400} \left(\frac{D_0}{\omega_r}\right)^{10} + \frac{4812476571577}{6357267735755489280000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(42)$$

$$C_1^{\text{IS3}} = \frac{2}{45} \left(\frac{D_0}{\omega_r}\right)^2 - \frac{17}{4860} \left(\frac{D_0}{\omega_r}\right)^4 + \frac{7991}{50038560} \left(\frac{D_0}{\omega_r}\right)^6 - \frac{6882901}{1543429375488} \left(\frac{D_0}{\omega_r}\right)^8 + \frac{13208297}{158752735764480} \left(\frac{D_0}{\omega_r}\right)^{10} - \frac{1119140771669}{1008604977307361280000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(43)$$

$$C_2^{\text{IS3}} = \frac{1}{180} \left(\frac{D_0}{\omega_r}\right)^2 + \frac{7}{19440} \left(\frac{D_0}{\omega_r}\right)^4 - \frac{181963}{5604318720} \left(\frac{D_0}{\omega_r}\right)^6 + \frac{34933061}{30868587509760} \left(\frac{D_0}{\omega_r}\right)^8 - \frac{9947191}{423340628705280} \left(\frac{D_0}{\omega_r}\right)^{10} + \frac{2495680997437}{7492494117140398080000} \left(\frac{D_0}{\omega_r}\right)^{12}$$

$$(44)$$

$$C_3^{\text{IS3}} = \frac{1}{4860} \left(\frac{D_0}{\omega_{\text{r}}}\right)^4 - \frac{24217}{2101619520} \left(\frac{D_0}{\omega_{\text{r}}}\right)^6 + \frac{193091}{514476458496} \left(\frac{D_0}{\omega_{\text{r}}}\right)^8 - \frac{653753}{79376367882240} \left(\frac{D_0}{\omega_{\text{r}}}\right)^{10} + \frac{26639914823}{208124836587233280000} \left(\frac{D_0}{\omega_{\text{r}}}\right)^{12}$$

$$(45)$$

8 Acknowledgements

480

485

We gratefully acknowledge MOF sample synthesis by Professor Peter Behrens and his co-workers Jann Lippke and Andreas Schaate (Leibniz Universität Hannover, Institut für Anorganische Chemie). The linkers used for the MOF samples were synthesized by Professor Adelheid Godt and Thomas Preuße (Universität Bielefeld, Fakultät für Chemie). We also thank Adelheid Godt for carefully reading the manuscript and her valuable suggestions.

Author contributions. GH conducted theoretical considerations and data analysis, RK carried out the DIPSHIFT experiments and was involved in data analysis, SP performed the CPMAS and HETCOR experiments, KS and EB supervised the research, discussed the results. All authors contributed to paper writing and approved the final manuscript version.

Data availability. The datasets generated and analyzed for this study as they appear in the figures of this article can be found in the Zenodo repository: https://doi.org/10.5281/zenodo.10149811

Competing interests. Kay Saalwächter is a member of the editorial board of Magnetic Resonance.

References

500

- Advanced Chemistry Development Inc.: ACD/C+H NMR Predictors and DB, www.acdlabs.com, 2017.
- Anderson, P. W. and Weiss, P. R.: Exchange Narrowing in Paramagnetic Resonance, Reviews of Modern Physics, 25, 269–276, https://doi.org/DOI 10.1103/RevModPhys.25.269, 1953.
 - Bärenwald, R., Achilles, A., Lange, F., Ferreira, T. M., and Saalwächter, K.: Applications of Solid-State NMR Spectroscopy for the Study of Lipid Membranes with Polyphilic Guest (Macro)Molecules, Polymers, 8, https://doi.org/ARTN 439 10.3390/polym8120439, 2016.
 - Bavykina, A., Kolobov, N., Khan, I. S., Bau, J. A., Ramirez, A., and Gascon, J.: Metal–Organic Frameworks in Heterogeneous Catalysis: Recent Progress, New Trends, and Future Perspectives, Chemical Reviews, 120, 8468–8535, https://doi.org/10.1021/acs.chemrev.9b00685, 2020.
 - Bignami, G. P. M., Davis, Z. H., Dawson, D. M., Morris, S. A., Russell, S. E., McKay, D., Parke, R. E., Iuga, D., Morris, R. E., and Ashbrook, S. E.: Cost-effective O-17 enrichment and NMR spectroscopy of mixed-metal terephthalate metal-organic frameworks, Chemical Science, 9, 850–859, https://doi.org/10.1039/c7sc04649a, 2018.
- Brunner, E. and Rauche, M.: Solid-state NMR spectroscopy: an advancing tool to analyse the structure and properties of metal-organic frameworks, Chemical Science, 11, 4297–4304, https://doi.org/10.1039/d0sc00735h, 2020.
 - Clough, S. and Gray, K. W.: Stochastic Theory of Nuclear Magnetic Resonance Line in Rotating Solids, Proceedings of the Physical Society of London, 79, 457, https://doi.org/Doi 10.1088/0370-1328/79/3/301, 1962.
 - Cobo, M. F., Reichert, D., Saalwachter, K., and deAzevedo, E. R.: A double-component Anderson-Weiss approach for describing NMR signals of mobile SIn units: Application to constant-time DIPSHIFT experiments, Journal of Magnetic Resonance, 248, 115–125, https://doi.org/10.1016/j.jmr.2014.09.009, 2014.
 - de Azevedo, E. R., Saalwächter, K., Pascui, O., De Souza, A. A., Bonagamba, T. J., and Reichert, D.: Intermediate motions as studied by solid-state separated local field NMR experiments, Journal of Chemical Physics, 128, https://doi.org/Artn 104505 10.1063/1.2831798, 2008.
 - Duer, M.: Solid-State NMR Spectroscopy: Principles and Applications, Blackwell Science Ltd., Oxford, 2002.
- 515 Ferey, G.: Hybrid porous solids: past, present, future, Chemical Society Reviews, 37, 191–214, https://doi.org/10.1039/b618320b, 2008.
 - Ferguson, D. B. and Haw, J. F.: Transient Methods for in-Situ Nmr of Reactions on Solid Catalysts Using Temperature Jumps, Analytical Chemistry, 67, 3342–3348, https://doi.org/DOI 10.1021/ac00114a034, 1995.
 - Fung, B. M., Khitrin, A. K., and Ermolaev, K.: An improved broadband decoupling sequence for liquid crystals and solids, Journal of Magnetic Resonance, 142, 97–101, https://doi.org/DOI 10.1006/jmre.1999.1896, 2000.
- Gao, F., Yan, R., Shu, Y., Cao, Q., and Zhang, L.: Strategies for the application of metal–organic frameworks in catalytic reactions, RSC Adv., 12, 10114–10125, https://doi.org/10.1039/D2RA01175A, 2022.
 - Hajjar, R., Volkringer, C., Loiseau, T., Guillou, N., Marrot, J., Ferey, G., Margiolaki, I., Fink, G., Morais, C., and Taulelle, F.: Ga-71 Slow-CTMAS NMR and Crystal Structures of MOF-Type Gallium Carboxylates with Infinite Edge-Sharing Octahedra Chains (MIL-120 and MIL-124), Chemistry of Materials, 23, 39–47, https://doi.org/10.1021/cm1025427, 2011.
- 525 He, P., Lucier, B. E. G., Terskikh, V. V., Shi, Q., Dong, J., Chu, Y., Zheng, A., Sutrisno, A., and Huang, Y.: Spies Within Metal-Organic Frameworks: Investigating Metal Centers Using Solid-State NMR, The Journal of Physical Chemistry C, 118, 23728–23744, https://doi.org/10.1021/jp5063868, 2014.

- Hempel, G., Sotta, P., Long, D., and Saalwächter, K.: Efficient polynomial analysis of magic-angle spinning sidebands and application to order parameter determination in anisotropic samples, Magnetic Resonance, 2, 589–606, https://doi.org/https://doi.org/10.5194/mr-2-589-530
 2021, 2021.
 - Hirschinger, J.: A simple analytical model to describe dynamic magic-angle spinning experiments, Concepts in Magnetic Resonance Part A, 28a, 307–320, https://doi.org/10.1002/cmr.a.20064, 2006.
 - Hoffmann, H. C., Paasch, S., Muller, P., Senkovska, I., Padmanaban, M., Glorius, F., Kaskel, S., and Brunner, E.: Chiral recognition in metal-organic frameworks studied by solid-state NMR spectroscopy using chiral solvating agents, Chemical Communications, 48, 10484–10486. https://doi.org/10.1039/c2cc35366k, 2012.
 - Horcajada, P., Serre, C., Vallet-Regi, M., Sebban, M., Taulelle, F., and Ferey, G.: Metal-organic frameworks as efficient materials for drug delivery, Angewandte Chemie-International Edition, 45, 5974–5978, https://doi.org/10.1002/anie.200601878, 2006.
 - Jain, M. G., Rajalakshmi, G., Agarwal, V., Madhu, P. K., and Mote, K. R.: On the direct relation between REDOR and DIPSHIFT experiments in solid-state NMR, Journal of Magnetic Resonance, 308, https://doi.org/ARTN 106563 10.1016/j.jmr.2019.07.050, 2019.
- Jiang, Y. J., Huang, J., Marx, S., Kleist, W., Hunger, M., and Baiker, A.: Effect of Dehydration on the Local Structure of Framework Aluminum Atoms in Mixed Linker MIL-53(Al) Materials Studied by Solid-State NMR Spectroscopy, Journal of Physical Chemistry Letters, 1, 2886–2890, https://doi.org/10.1021/jz1010835, 2010.
 - Kaskel, S.: The Chemistry of Metal-Organic Frameworks, Wiley-VCH, Weinheim, 2016.

- Ke, F., Yuan, Y. P., Qiu, L. G., Shen, Y. H., Xie, A. J., Zhu, J. F., Tian, X. Y., and Zhang, L. D.: Facile fabrication of magnetic metal-organic framework nanocomposites for potential targeted drug delivery, Journal of Materials Chemistry, 21, 3843–3848, https://doi.org/10.1039/c0jm01770a, 2011.
 - Kitagawa, S., Kitaura, R., and Noro, S.-i.: Functional Porous Coordination Polymers, Angew. Chem. Intern. Ed., 43, 2334–2375, https://doi.org/10.1002/anie.200300610, 2004.
- Klein, N., Hoffmann, H. C., Cadiau, A., Getzschmann, J., Lohe, M. R., Paasch, S., Heydenreich, T., Adil, K., Senkovska, I., Brunner, E., and Kaskel, S.: Structural flexibility and intrinsic dynamics in the M-2(2,6-ndc)(2)(dabco) (M = Ni, Cu, Co, Zn) metal-organic frameworks, Journal of Materials Chemistry, 22, 10 303–10 312, https://doi.org/10.1039/c2im15601f, 2012.
 - Lawson, H. D., Walton, S. P., and Chan, C.: Metal-Organic Frameworks for Drug Delivery: A Design Perspective, ACS Applied Materials & Interfaces, 13, 7004–7020, https://doi.org/10.1021/acsami.1c01089, 2021.
 - Lee, W. and Goldburg, W.: Phys. Rev, 140, A1261–A1271, <=75:[L4] (Kop->FGB ****-**), 1965.
- Lesage, A., Sakellariou, D., Steuernagel, S., and Emsley, L.: Carbon-proton chemical shift correlation in solid-state NMR by through-bond multiple-quantum spectroscopy, Journal of the American Chemical Society, 120, 13 194–13 201, https://doi.org/DOI 10.1021/ja983048+, 1998a.
 - Lesage, A., Steuernagel, S., and Emsley, L.: Carbon-13 spectral editing in solid-state NMR using heteronuclear scalar couplings, Journal of the American Chemical Society, 120, 7095–7100, https://doi.org/DOI 10.1021/ja981019t, 1998b.
- Li, H., Li, L., Lin, R.-B., Zhou, W., Zhang, Z., Xiang, S., and Chen, B.: Porous metal-organic frameworks for gas storage and separation: Status and challenges, EnergyChem, 1, 100 006, https://doi.org/https://doi.org/10.1016/j.enchem.2019.100006, 2019.
 - Lieder, C., Opelt, S., Dyballa, M., Henning, H., Klemm, E., and Hunger, M.: Adsorbate Effect on AlO4(OH)(2) Centers in the Metal-Organic Framework MIL-53 Investigated by Solid-State NMR Spectroscopy, Journal of Physical Chemistry C, 114, 16596–16602, https://doi.org/10.1021/jp105700b, 2010.

- Lippke, J., Brosent, B., von Zons, T., Virmani, E., Lilienthal, S., Preuße, T., Hülsmann, M., Schneider, A. M., Wuttke, S., Behrens, P., and Godt, A.: Expanding the Group of Porous Interpenetrated Zr-Organic Frameworks (PIZOFs) with Linkers of Different Lengths, Inorganic Chemistry, 56, 748–761, https://doi.org/10.1021/acs.inorgchem.6b01814, 2017.
 - Liu, X., Shan, Y., Zhang, S., Kong, Q., and Pang, H.: Application of metal organic framework in wastewater treatment, Green Energy and Environment, 8, 698–721, https://doi.org/10.1016/j.gee.2022.03.005, 2023.
- Loiseau, T., Muguerra, H., Ferey, G., Haouas, M., and Taulelle, F.: Synthesis and structural characterization of a new open-framework zinc terephthalate Zn-3(OH)(2)(bdc)(2) .2DEF, with infinite Zn-(mu(3)-OH)-Zn chains, Journal of Solid State Chemistry, 178, 621–628, https://doi.org/10.1016/j.jssc.2004.12.004, 2005.
 - Lucier, B. E. G., Chen, S. S., and Huang, Y. N.: Characterization of Metal-Organic Frameworks: Unlocking the Potential of Solid-State NMR, Accounts of Chemical Research, 51, 319–330, https://doi.org/10.1021/acs.accounts.7b00357, 2018.
- 575 Maranescu, B. and Visa, A.: Applications of Metal-Organic Frameworks as Drug Delivery Systems, International Journal of Molecular Sciences, 23, https://doi.org/10.3390/ijms23084458, 2022.
 - Maurin, G., Serre, C., Cooper, A., and Férey, G.: The new age of MOFs and of their porous-related solids, Chem. Soc. Rev., 46, 3104–3107, https://doi.org/10.1039/C7CS90049J, 2017.
 - Mehring, M.: Principles of High Resolution NMR in Solids, Springer, 1983.
- 580 Metz, G., Wu, X. L., and Smith, S. O.: Ramped-Amplitude Cross-Polarization in Magic-Angle-Spinning Nmr, Journal of Magnetic Resonance Series A, 110, 219–227, https://doi.org/DOI 10.1006/jmra.1994.1208, 1994.
 - Mowat, J. P. S., Miller, S. R., Slawin, A. M. Z., Seymour, V. R., Ashbrook, S. E., and Wright, P. A.: Synthesis, characterisation and adsorption properties of microporous scandium carboxylates with rigid and flexible frameworks, Microporous and Mesoporous Materials, 142, 322–333, https://doi.org/10.1016/j.micromeso.2010.12.016, 2011.
- Munowitz, M. G., Griffin, R. G., Bodenhausen, G., and Huang, T. H.: Two-Dimensional Rotational Spin-Echo Nuclear Magnetic-Resonance in Solids - Correlation of Chemical-Shift and Dipolar Interactions, Journal of the American Chemical Society, 103, 2529–2533, https://doi.org/DOI 10.1021/ja00400a007, 1981.
 - Paasch, S. and Brunner, E.: Trends in solid-state NMR spectroscopy and their relevance for bioanalytics, Analytical and Bioanalytical Chemistry, 398, 2351–2362, https://doi.org/10.1007/s00216-010-4037-5, 2010.
- Pascanu, V., González Miera, G., Inge, A. K., and Martín-Matute, B.: Synthesis of metal-organic frameworks: A mini review, Korean Journal of Chemical Engineering, 9, 17–29, https://doi.org/10.1021/jacs.9b00733, 2019.
 - Petrov, O. V., Chlan, V., Rohlíček, J., Demel, J., Veselý, J., and Lang, J.: Exploring Structural Disorders in Aluminum-Containing Metal—Organic Frameworks: Comparison of Solid-State 27Al NMR Powder Spectra to DFT Calculations on Bulk Periodic Structures, The Journal of Physical Chemistry C, 124, 12 569–12 579, https://doi.org/10.1021/acs.jpcc.0c03000, 2020.
- 595 Pines, A., Gibby, M., and Waugh, J.: Proton-Enhanced Nmr of Dilute Spins in Solids, Journal of Chemical Physics, 59, 569–590, <GotoISI>: //A1973Q329300001, 1973.
 - Pursch, M., Sander, L. C., and Albert, K.: Chain order and mobility of high-density C-18 phases by solid-state NMR spectroscopy and liquid chromatography, Analytical Chemistry, 68, 4107–4113, https://doi.org/DOI 10.1021/ac9606113, 1996.
- Remya, V. R. and Kurian, M.: Synthesis and catalytic applications of metal–organic frameworks: a review on recent literature, International Nano Letters, 141, 7223–7234, https://doi.org/10.1007/s40089-018-0255-1, 2019.
 - Renault, M., Cukkemane, A., and Baldus, M.: Solid-State NMR Spectroscopy on Complex Biomolecules, Angewandte Chemie-International Edition, 49, 8346–8357, https://doi.org/10.1002/anie.201002823, 2010.

- Roy, P., Schaate, A., Behrens, P., and Godt, A.: Post-Synthetic Modification of Zr-Metal-Organic Frameworks through Cycloaddition Reactions, Chemistry-a European Journal, 18, 6979–6985, https://doi.org/10.1002/chem.201103288, 2012.
- Schaate, A., Roy, P., Preusse, T., Lohmeier, S. J., Godt, A., and Behrens, P.: Porous Interpenetrated Zirconium-Organic Frameworks (PIZOFs): A Chemically Versatile Family of Metal-Organic Frameworks, Chemistry-a European Journal, 17, 9320–9325, https://doi.org/10.1002/chem.201101015, 2011.
 - Schaefer, J., Mckay, R. A., and Stejskal, E. O.: Dipolar Rotational Spin-Echo C-13 Nmr of Polymers, Journal of Magnetic Resonance, 52, 123–129, https://doi.org/Doi 10.1016/0022-2364(83)90262-7, 1983.
- Schulze, D., Ernst, H., Fenzke, D., Meiler, W., and Pfeifer, H.: Applicability of the Nmr Cross-Polarization Technique to Separate Rigid and Mobile Components in Coal Structure, Journal of Physical Chemistry, 94, 3499–3502, https://doi.org/DOI 10.1021/j100372a026, 1990.
 - Simonutti, R., Comotti, A., Bracco, S., and Sozzani, P.: Surfactant organization in MCM-41 mesoporous materials as studied by C-13 and Si-29 solid-state NMR, Chemistry of Materials, 13, 771–777, https://doi.org/10.1021/cm001088i, 2001.
 - Sindorf, D. W. and Maciel, G. E.: Solid-State Nmr-Studies of the Reactions of Silica Surfaces with Polyfunctional Chloromethylsilanes and Ethoxymethylsilanes, Journal of the American Chemical Society, 105, 3767–3776, https://doi.org/DOI 10.1021/ja00350a003, 1983.

615

- Tranchemontagne, D. J., Mendoza-Cortés, J. L., O'Keeffe, M., and Yaghi, O. M.: Secondary building units, nets and bonding in the chemistry of metal–organic frameworks, Chem. Soc. Rev., 38, 1257–1283, https://doi.org/10.1039/B817735J, 2009.
- Volkringer, C., Loiseau, T., Ferey, G., Morais, C. M., Taulelle, F., Montouillout, V., and Massiot, D.: Synthesis, crystal structure and Ga-71 solid state NMR of a MOF-type gallium trimesate (MIL-96) with mu(3)-oxo bridged trinuclear units and a hexagonal 18-ring network, Microporous and Mesoporous Materials, 105, 111–117, https://doi.org/10.1016/j.micromeso.2007.05.018, 2007.
- Witherspoon, V. J., Xu, J., and Reimer, J. A.: Solid-State NMR Investigations of Carbon Dioxide Gas in Metal-Organic Frameworks: Insights into Molecular Motion and Adsorptive Behavior, Chemical Reviews, 118, 10033–10048, https://doi.org/10.1021/acs.chemrev.7b00695, 2018.
- Wittmann, T., Tschense, C. B. L., Zappe, L., Koschnick, C., Siegel, R., Staglich, R., Lotsch, B. V., and Senker, J.: Selective host-guest interactions in metal-organic frameworks via multiple hydrogen bond donor-acceptor recognition sites, Journal of Materials Chemistry A, 7, 10 379–10 388, https://doi.org/10.1039/c8ta12190g, 2019.
 - Wong, Y. T. A., Martins, V., Lucier, B. E. G., and Huang, Y. N.: Solid-State NMR Spectroscopy: A Powerful Technique to Directly Study Small Gas Molecules Adsorbed in Metal-Organic Frameworks, Chemistry-a European Journal, 25, 1848–1853, https://doi.org/10.1002/chem.201803866, 2019.
- Wurl, A., Saalwächter, K., and Mendes Ferreira, T.: Time-domain proton-detected local-field NMR for molecular structure determination in complex lipid membranes, Magnetic Resonance, 4, 115–127, https://doi.org/10.5194/mr-4-115-2023, 2023.
 - Yan, Y., Kolokolov, D. I., da Silva, I., Stepanov, A. G., Blake, A. J., Dailly, A., Manuel, P., Tang, C. C., Yang, S. H., and Schroder, M.: Porous Metal-Organic Polyhedral Frameworks with Optimal Molecular Dynamics and Pore Geometry for Methane Storage, Journal of the American Chemical Society, 139, 13 349–13 360, https://doi.org/10.1021/jacs.7b05453, 2017.